




# Detail Gradation Statistical Summary Report

**Plant** 1030-Haines City Mine (FDOT Pit #16-024)  
**Product** 1009-Concrete Sand  
**Specification**  
**Period** 03/07/2019 - 03/14/2019

Sieve/Test	Tests	Average	Min	Max	Range	St Dev	Target	Specification	PWS
#4 (4.75mm)	5	0.0	0.0	0.0	0.0	0.00			
#8 (2.36mm)	5	0.2	0.0	0.6	0.6	0.23			
#16 (1.18mm)	5	6.0	3.9	9.1	5.2	1.89			
#30 (0.6mm)	5	34.9	29.6	39.7	10.1	4.19			
#50 (0.3mm)	5	62.4	55.8	68.8	13.0	5.24			
#100 (0.15mm)	5	93.6	91.4	96.2	4.8	1.86			
#200 (75µm)	5	99.9	99.9	100.0	0.1	0.05			
Pan	5	100.0	100.0	100.0	0.0	0.00			
FM	5	1.97	1.83	2.14	0.31	0.115			
Total Moisture	5	3.1	2.8	3.5	0.7	0.28			

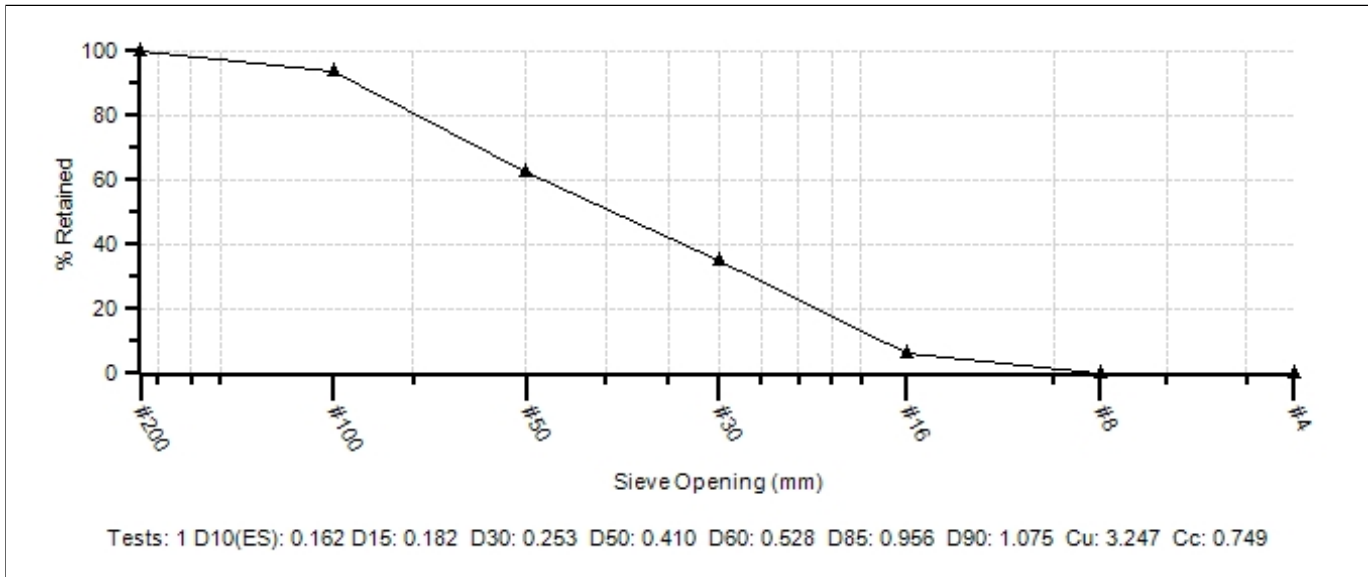

**Comments**

**Query** Query Selections  
 Date Created 03/14/2019  
 Date Range 03/07/2019 - 03/14/2019  
 Plant Haines City Mine (FDOT Pit #16-024)-1030  
 Sample Type Shipping