




# Basic Quality Statistical Summary Report

**Plant** 1070-Independent South Mine (FDOT Pit#11-298)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 08/29/2019 - 09/05/2019

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	4	100.0	0.00		95-100
#8 (2.36mm)	4	99.9	0.08		85-100
#16 (1.18mm)	4	95.3	1.08	67-98	65-99
#30 (0.6mm)	4	73.2	4.62	27-79	25-80
#50 (0.3mm)	4	33.8	6.96	7-38	5-40
#100 (0.15mm)	4	5.1	1.59	0-6	0-7
#200 (75µm)	4	0.2	0.13		0-4
Pan	4	0.0	0.00		
FM	4	1.927	0.1404	1.87-2.18\2	1.85-2.2

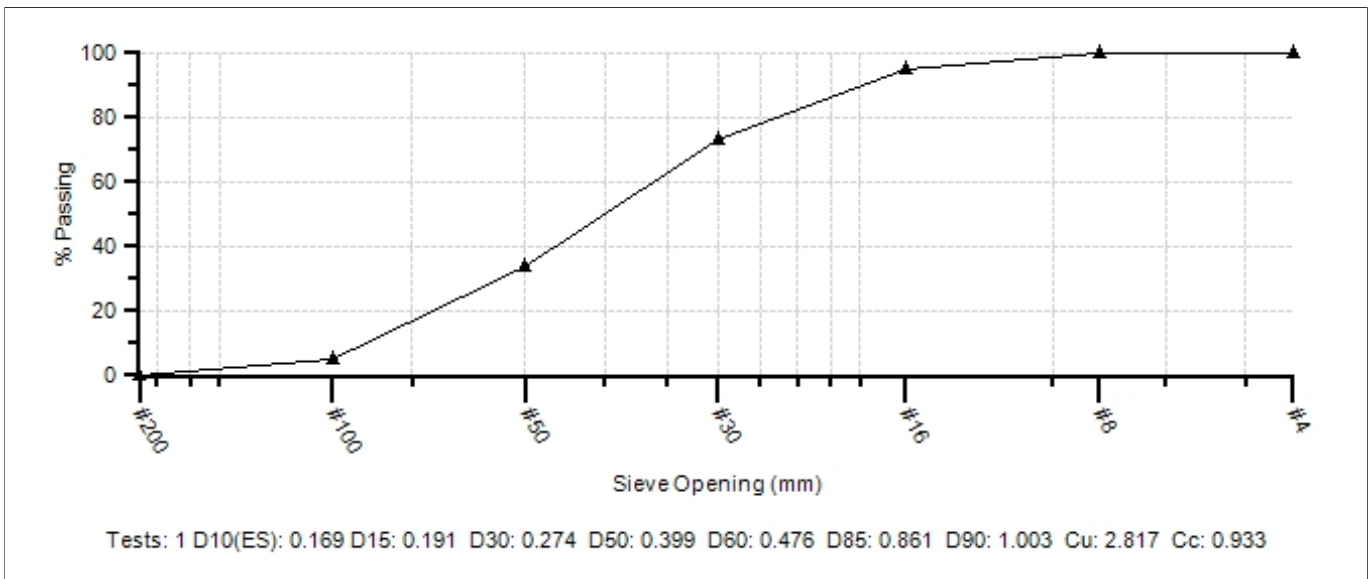

**Query** Query Selections  
 Date Created 09/05/2019  
 Date Range 08/29/2019 - 09/05/2019  
 Plant Independent South Mine (FDOT Pit#11-298)