




# Basic Quality Statistical Summary Report

**Plant** 1070-Independent South Mine (FDOT Pit#11-298)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 03/19/2020 - 03/26/2020

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	72	100.0	0.00		95-100
#8 (2.36mm)	73	99.8	0.06		85-100
#16 (1.18mm)	73	93.8	1.27	67-98	65-99
#30 (0.6mm)	73	69.2	4.25	27-79	25-80
#50 (0.3mm)	73	31.9	5.59	7-38	5-40
#100 (0.15mm)	73	5.3	1.80	0-6	0-7
#200 (75µm)	73	0.2	0.10		0-4
Pan	73	0.0	0.00		
FM	73	2.001	0.1196	1.87-2.18\2	1.85-2.2

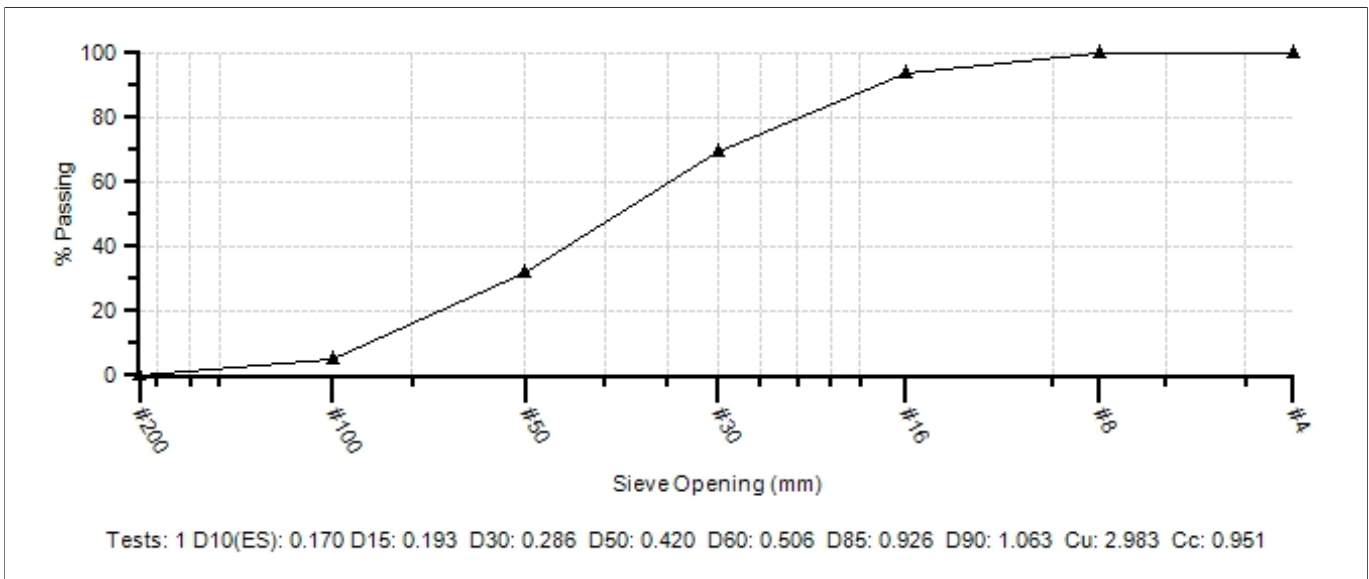

**Query** Query Selections  
 Date Created 03/26/2020  
 Date Range 03/19/2020 - 03/26/2020  
 Plant Independent South Mine (FDOT Pit#11-298)