




# Basic Quality Statistical Summary Report

**Plant** 1070-Independent South Mine (FDOT Pit#11-298)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 12/10/2020 - 12/17/2020

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	30	100.0	0.00		95-100
#8 (2.36mm)	30	99.6	0.25		85-100
#16 (1.18mm)	30	93.8	2.30	67-98	65-99
#30 (0.6mm)	30	68.6	5.03	27-79	25-80
#50 (0.3mm)	30	30.3	6.13	7-38	5-40
#100 (0.15mm)	30	4.0	2.01	0-6	0-7
#200 (75µm)	30	0.2	0.13		0-4
Pan	30	0.0	0.00		
FM	30	2.038	0.1211	1.87-2.18\2	1.85-2.2

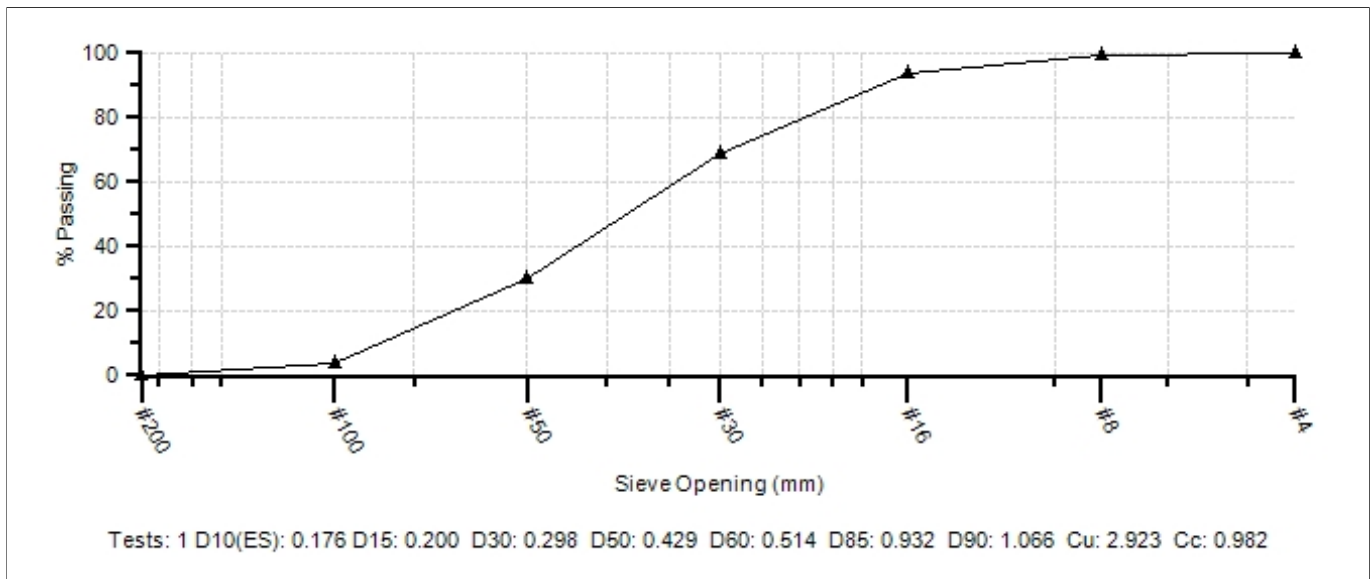

**Query** Query Selections  
 Date Created 12/17/2020  
 Date Range 12/10/2020 - 12/17/2020  
 Plant Independent South Mine (FDOT Pit#11-298)