




# Basic Quality Statistical Summary Report

**Plant** 1050-Independent North Mine (FDOT Pit #11-490)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 10/28/2021 - 11/04/2021

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	2	100.0	0.00		95-100
#8 (2.36mm)	2	99.4	0.00		85-100
#16 (1.18mm)	2	92.9	0.28	67-98	65-99
#30 (0.6mm)	2	68.8	1.91	27-79	25-80
#50 (0.3mm)	2	28.5	9.05	7-38	5-40
#100 (0.15mm)	2	3.1	2.69	0-6	0-7
#200 (75µm)	2	0.0	0.07		0-4
Pan	2	0.0	0.00		
<hr/>					
Total Moisture	2	6.8	0.07		
FM	2	2.08	0.134	1.87-2.18\2	1.85-2.2

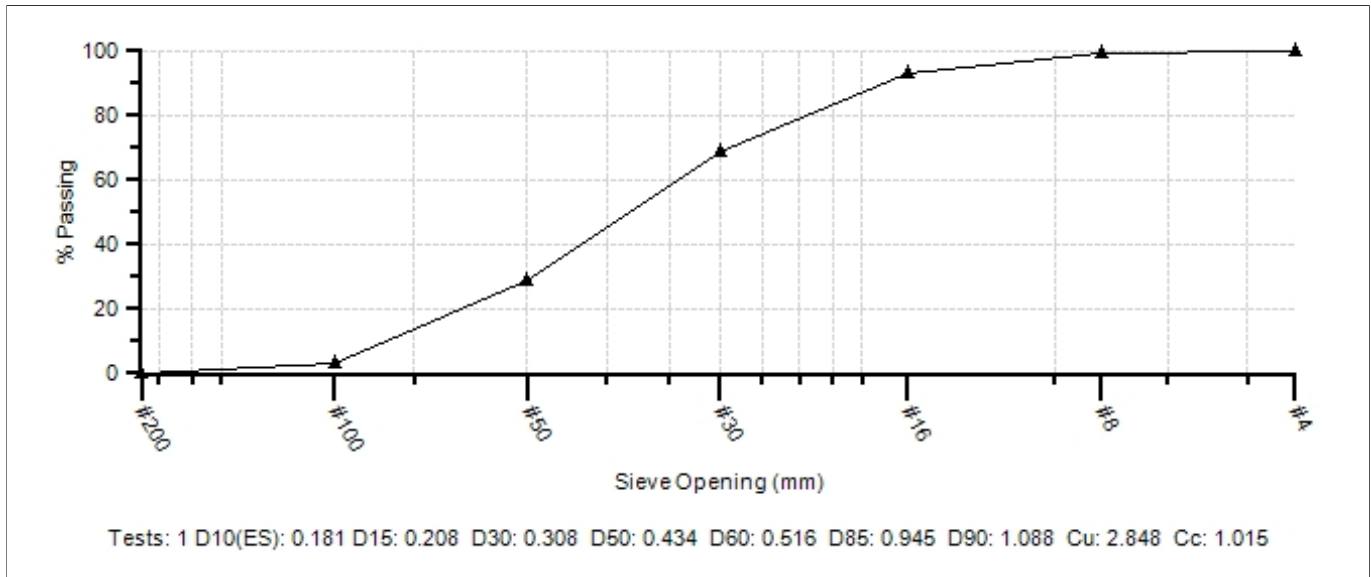

**Query** Query Selections  
 Date Created 11/04/2021  
 Date Range 10/28/2021 - 11/04/2021  
 Plant Independent North Mine (FDOT Pit #11-490)  
 Sample Type Shipping