




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 10/28/2021 - 11/04/2021

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	10	100	0.0	95-100	95-100
#8 (2.36mm)	10	100	0.0	85-100	85-100
#16 (1.18mm)	10	93	0.5	67-96	65-97
#30 (0.6mm)	10	59	3.8	27-68	25-70
#50 (0.3mm)	10	22	4.5	7-33	5-35
#100 (0.15mm)	10	2	0.8	0-6	0-7
#200 (75µm)	10	0	0.3	0-4	0-4
Pan	10	0	0.0		
Wash Loss (#200/75um)	1	0.53			
Total Moisture	10	4.2	0.39		
FM	10	2.24	0.089	2.3	2.1-2.5

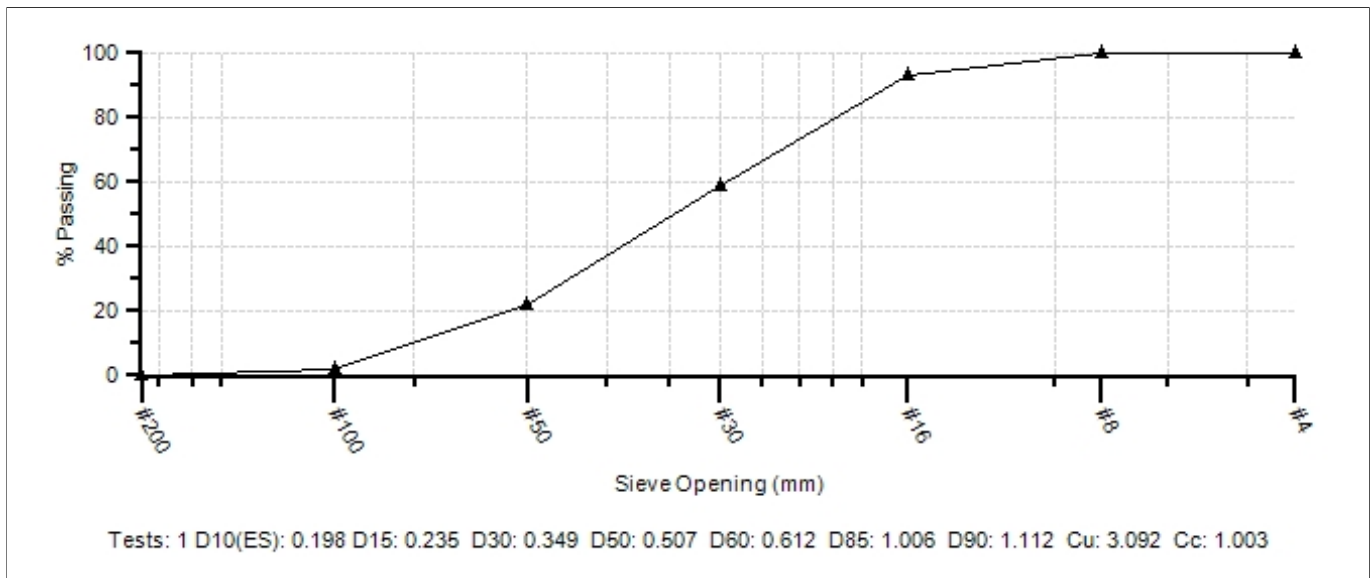

Query Query Selections
 Date Created 11/04/2021
 Date Range 10/28/2021 - 11/04/2021
 Plant Green Bay Mine (FDOT Pit #16-608)
 Sample Type Shipping
 Agency Florida DOT MAC