




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 12/27/2021 - 01/04/2022

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	9	100	0.0	95-100	95-100
#8 (2.36mm)	9	100	0.0	85-100	85-100
#16 (1.18mm)	9	91	1.0	67-96	65-97
#30 (0.6mm)	9	56	2.8	27-68	25-70
#50 (0.3mm)	9	22	3.7	7-33	5-35
#100 (0.15mm)	9	2	0.7	0-6	0-7
#200 (75µm)	9	0	0.0	0-4	0-4
Pan	9	0	0.0		
Grad Loss	9	0.070	0.0656		
-#200 (75um)	2	0.17	0.127		
Wash Loss (#200/75um)	2	0.14	0.113		
Color	1	4			1-5
Total Moisture	9	3.4	0.66		
FM	9	2.29	0.084	2.3	2.1-2.5

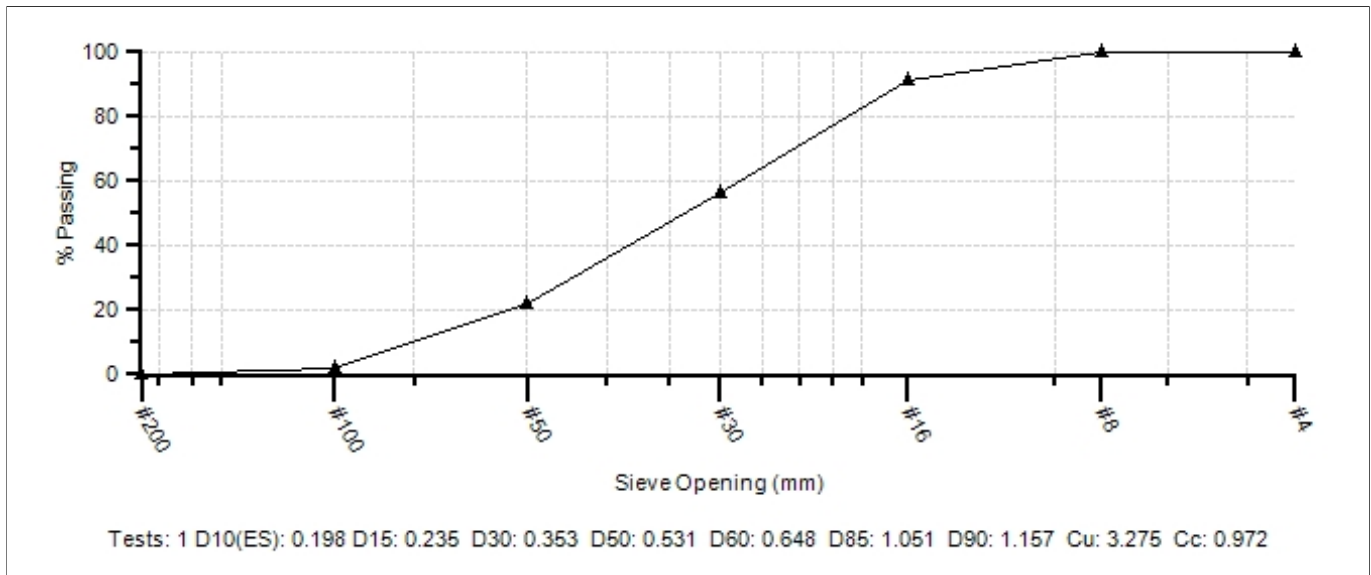

Query Query Selections
 Date Created 01/04/2022
 Date Range 12/27/2021 - 01/04/2022
 Plant Green Bay Mine (FDOT Pit #16-608)
 Sample Type Shipping