




Basic Quality Statistical Summary Report

Plant 1210-Liberty Sand Mine
Product 117-GDOT 10NS Concrete Sand
Specification GADOT 10NS
Period 12/27/2021 - 01/04/2022

Sieve/Test	Tests	Average	St Dev	Target	Specification
3/8" (9.5mm)	8	100.00	0.000		
#4 (4.75mm)	8	99.41	0.169		95-100
#8 (2.36mm)	8	92.49	1.033		
#16 (1.18mm)	8	71.63	3.172		45-95
#30 (0.6mm)	8	43.61	4.043		
#50 (0.3mm)	8	18.66	3.183		5-30
#100 (0.15mm)	8	4.73	1.569		0-10
#200 (75µm)	8	0.09	0.032		0-3
Pan	8	0.00	0.000		
-#200 (75µm)	1	0.13			
Grad Loss	8	0.000	0.0000		
Wash Loss (#200/75µm)	1	0.08			
Color	1	1			
FM	8	2.69	0.103	2.65-3.05\2.85	
Total Moisture	8	3.8	0.45	0-5\4	0-6

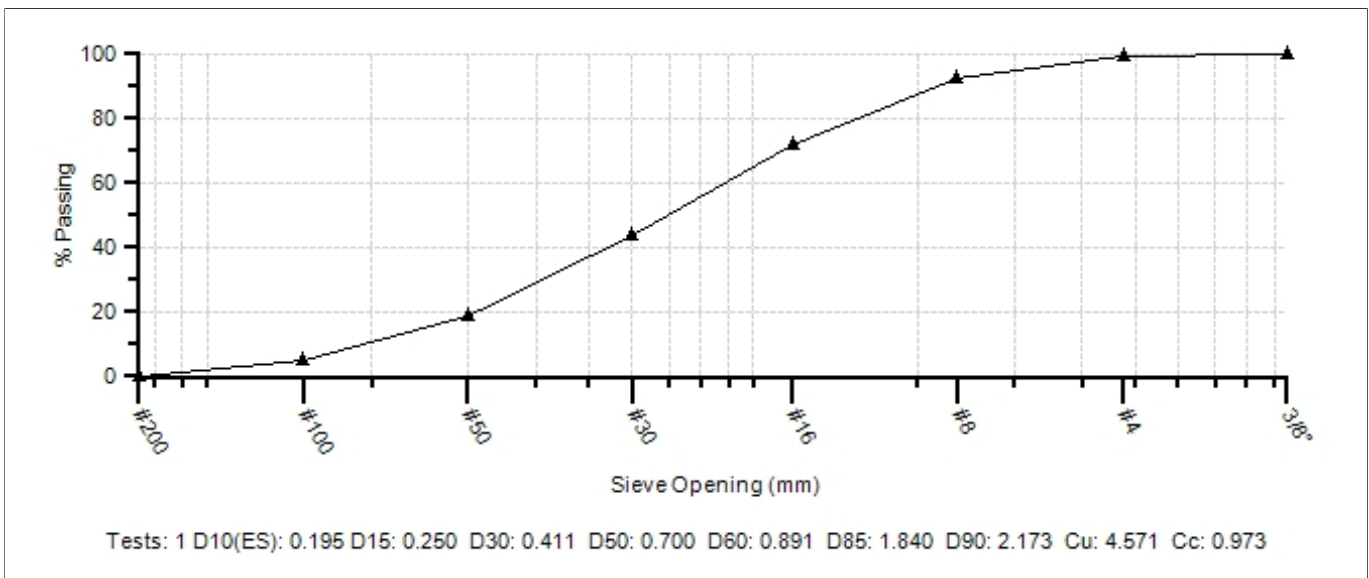

Query Query Selections
 Date Created 01/04/2022
 Date Range 12/27/2021 - 01/04/2022
 Plant Liberty Sand Mine
 Sample Type Shipping