




Basic Quality Statistical Summary Report

Plant 1070-Independent South Mine (FDOT Pit#11-298)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 10/18/2022 - 10/25/2022

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	10	100	0.0	95-100	95-100
#8 (2.36mm)	10	100	0.4	85-100	85-100
#16 (1.18mm)	10	94	0.7	67-96	65-97
#30 (.6mm)	10	62	3.6	27-68	25-70
#50 (.3mm)	10	16	3.9	7-33	5-35
#100 (.15mm)	10	1	0.9	0-7	0-7
#200 (75µm)	10	0	0.0	0-4	0-4
Pan	10	0	0.0		
FM	10	2.277	0.0827	2.08-2.4\2.25	2.05-2.45

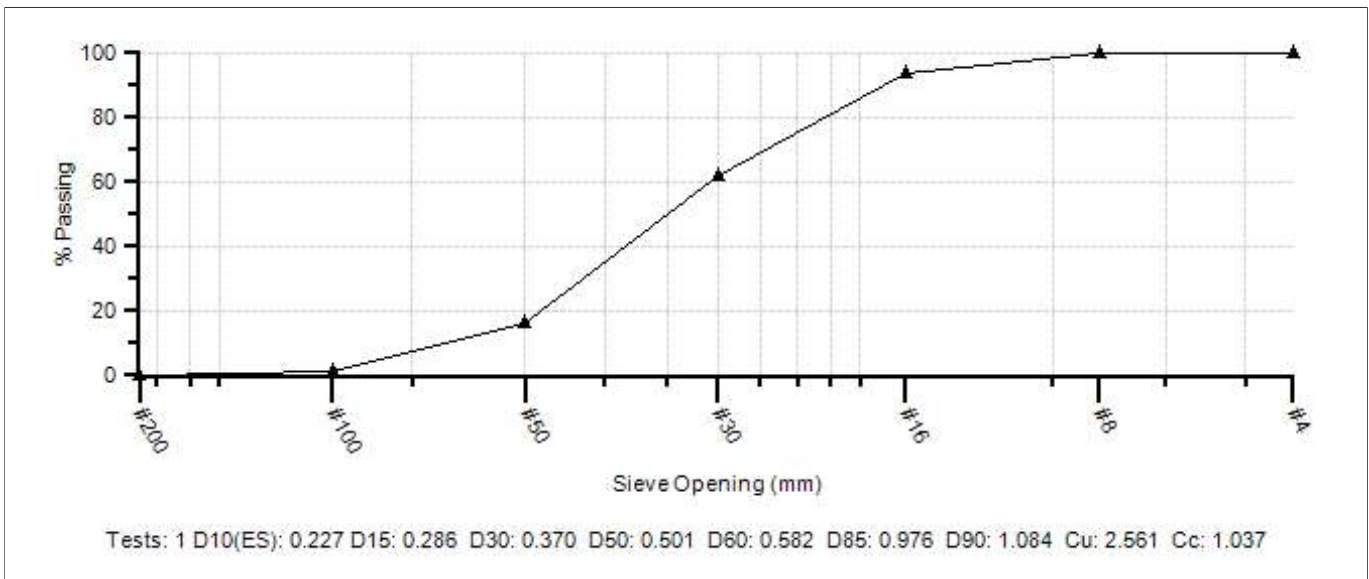

Query

Query Selections
Date Created 10/25/2022
Date Range 10/18/2022 - 10/25/2022
Plant Independent South Mine (FDOT Pit#11-298)
Sample Type Shipping