




# Basic Quality Statistical Summary Report

**Plant** 2010-Ortona Sand Company (FDOT Pit # 05-045)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 10/18/2022 - 10/25/2022

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	5	100.0	0.00	95-100	
#8 (2.36mm)	5	99.9	0.04	85-100	
#16 (1.18mm)	5	97.7	0.58	65-99	
#30 (.6mm)	5	67.9	3.00	25-70	
#50 (.3mm)	5	27.5	5.43	5-35	
#100 (.15mm)	5	2.5	0.94	0-7	
#200 (75µm)	5	0.0	0.00		
Pan	5	0.0	0.00		
FM	5	2.05	0.091		
Total Moisture	5	3.9	0.41		

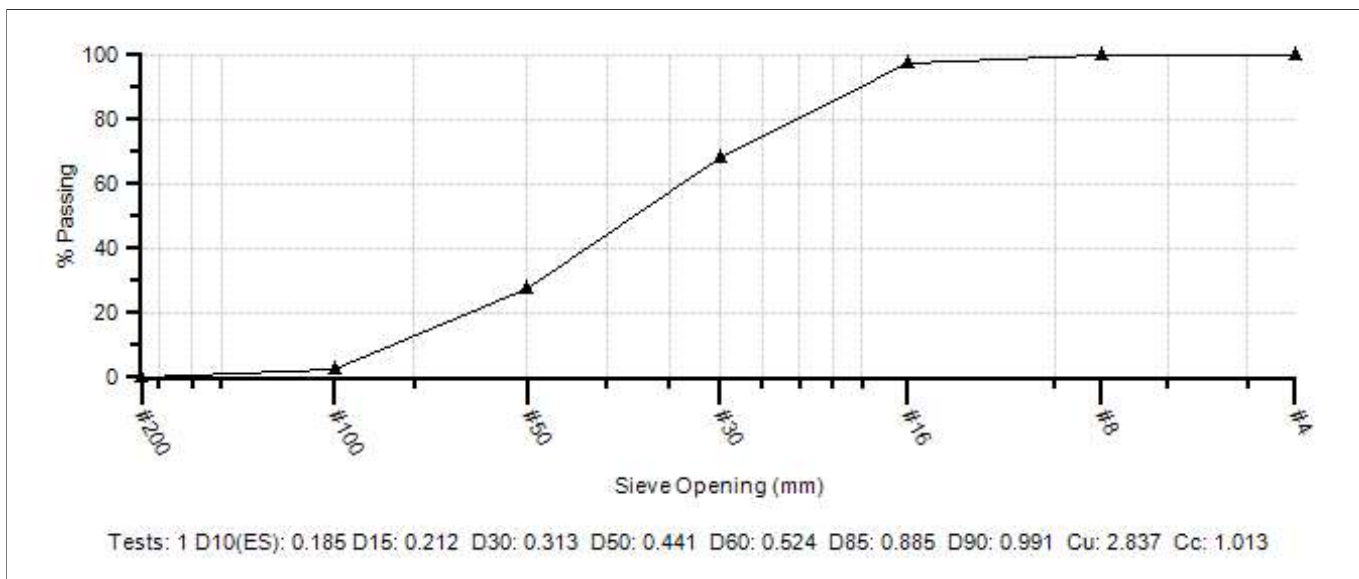

**Query**

Query Selections  
Date Created 10/25/2022  
Date Range 10/18/2022 - 10/25/2022  
Plant Ortona Sand Company (FDOT Pit # 05-045)  
Sample Type Shipping