




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 03/29/2024 - 04/05/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	9	100	0.0	95-100	95-100
#8 (2.36mm)	9	100	0.0	85-100	85-100
#16 (1.18mm)	9	95	0.7	67-96	65-97
#30 (.6mm)	9	62	2.9	27-68	25-70
#50 (.3mm)	9	19	2.9	7-33	5-35
#100 (.15mm)	9	1	0.5	0-6	0-7
#200 (75µm)	9	0	0.0	0-4	0-4
Pan	9	0	0.0		
FM	9	2.24	0.040	2.3	2.1-2.5
Wash Loss (#200/75um)	1	0.05			
Total Moisture	9	3.8	0.91		
Color	1	3			1-5

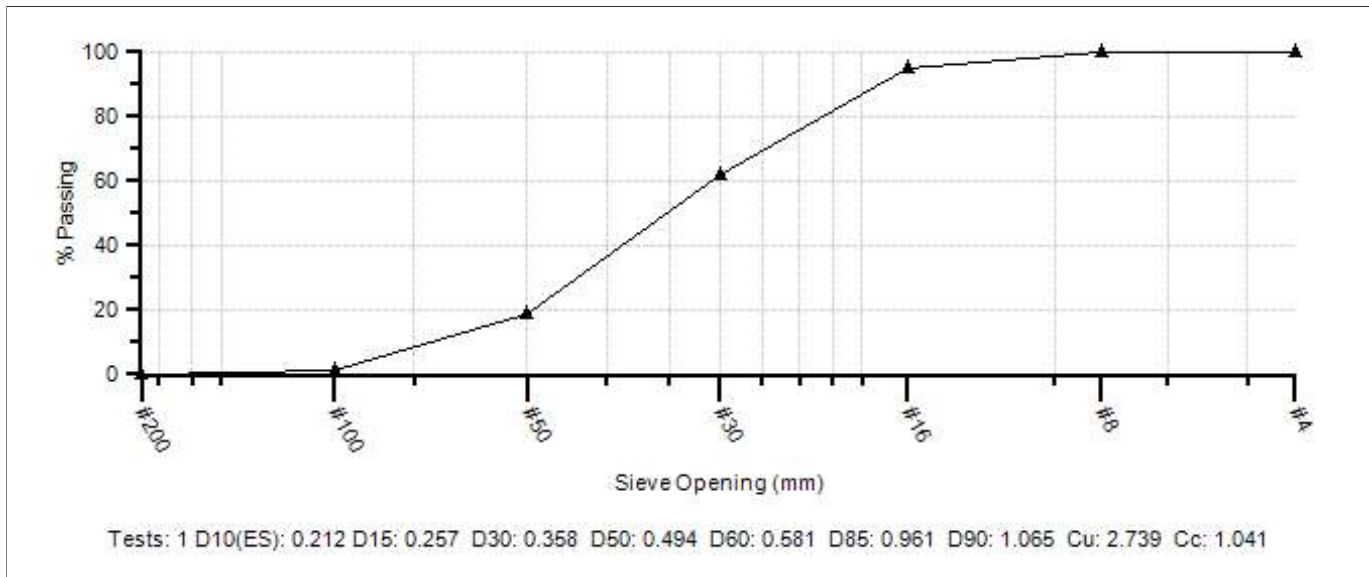

Query

Query Selections
Date Created 04/05/2024
Date Range 03/29/2024 - 04/05/2024
Plant Green Bay Mine (FDOT Pit #16-608)
Sample Type Shipping
Agency Florida DOT MAC