




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 04/17/2024 - 04/24/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	12	100	0.0	95-100	95-100
#8 (2.36mm)	12	100	0.0	85-100	85-100
#16 (1.18mm)	12	95	1.1	67-96	65-97
#30 (.6mm)	12	60	3.7	27-68	25-70
#50 (.3mm)	12	21	5.0	7-33	5-35
#100 (.15mm)	12	1	0.8	0-6	0-7
#200 (75µm)	12	0	0.0	0-4	0-4
Pan	12	0	0.0		
FM	12	2.24	0.085	2.3	2.1-2.5
-#200 (75um)	1	0.05			
Grad Loss	12	0.031	0.0512		
Wash Loss (#200/75um)	1	0.05			
Total Moisture	12	3.0	0.48		
Color	1	3			1-5
D10 (ES)	12	0.2105	0.02382		
D50	12	0.51	0.032		
D60	12	0.61	0.040		
Cc	12	0.97	0.064		
Cu	12	2.90	0.271		

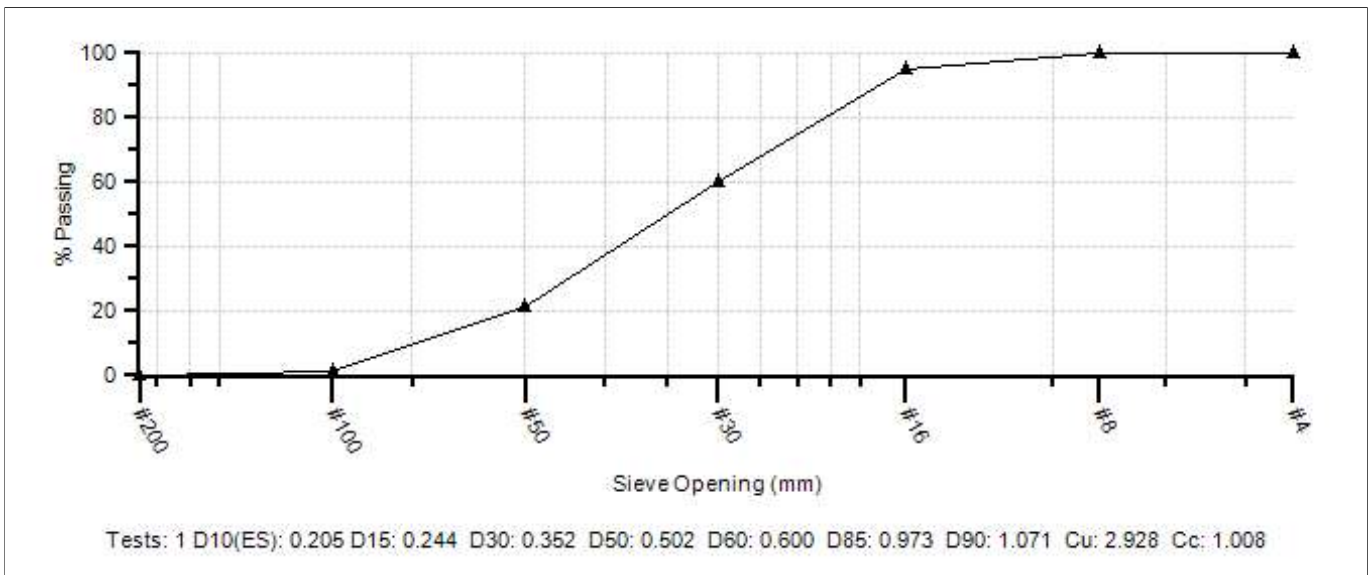

Query

Query Selections
Date Created 04/24/2024
Date Range 04/17/2024 - 04/24/2024
Plant Green Bay Mine (FDOT Pit #16-608)
Sample Type Shipping