




Basic Quality Statistical Summary Report

Plant 1210-Liberty Sand Mine
Product 117-GDOT 10NS Concrete Sand
Specification GADOT 10NS
Period 04/17/2024 - 04/24/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
3/8" (9.5mm)	3	100.00	0.000		
#4 (4.75mm)	7	99.50	0.145		95-100
#8 (2.36mm)	7	92.58	1.141		
#16 (1.18mm)	7	70.95	3.662		45-95
#30 (.6mm)	7	41.55	6.709		
#50 (.3mm)	7	20.27	6.636		5-30
#100 (.15mm)	7	4.70	1.864		0-10
#200 (75µm)	7	0.23	0.044		0-3
Pan	7	0.00	0.000		
FM	7	2.70	0.189	2.4-2.85\2.65	
-#200 (75µm)	1	0.22			
Grad Loss	7	0.067	0.0704		
Wash Loss (#200/75µm)	1	0.20			
Total Moisture	6	3.5	0.63	0-5\4	0-6
Color	1	1			
D10 (ES)	7	0.20	0.050		
D50	7	0.72	0.093		
Cu	7	4.60	0.597		

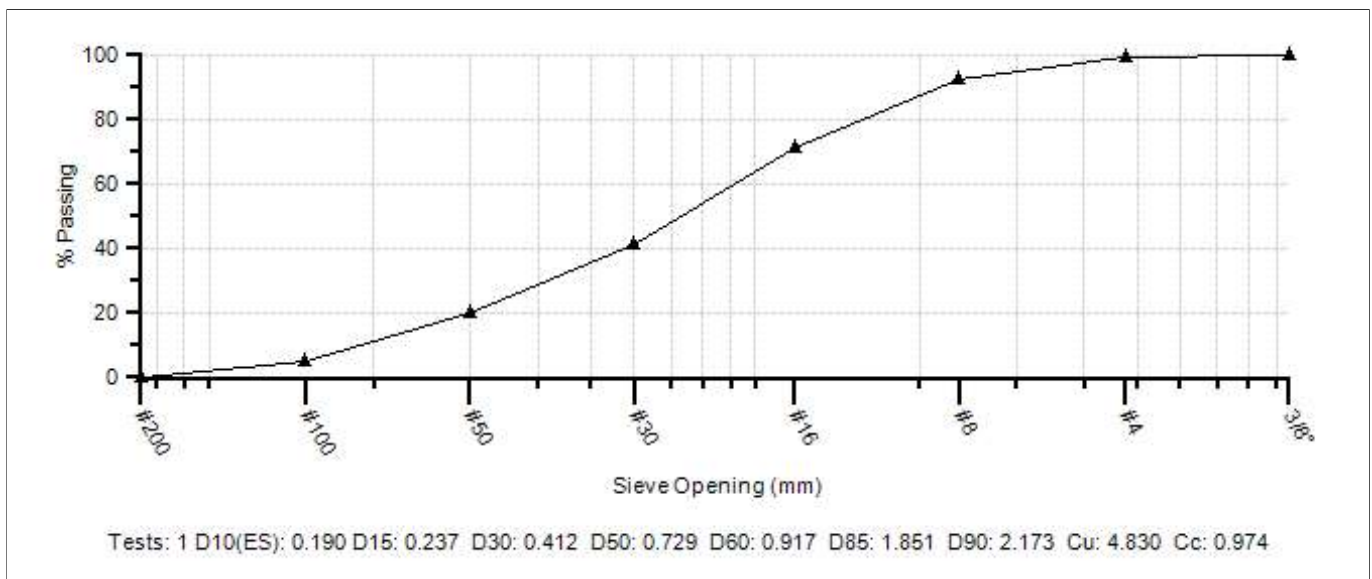

Query

Query Selections
Date Created 04/24/2024
Date Range 04/17/2024 - 04/24/2024
Plant Liberty Sand Mine
Sample Type Shipping