




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 04/28/2024 - 05/03/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	10	100	0.0	95-100	95-100
#8 (2.36mm)	10	100	0.0	85-100	85-100
#16 (1.18mm)	10	95	1.0	67-96	65-97
#30 (.6mm)	10	67	6.4	27-68	25-70
#50 (.3mm)	10	24	3.8	7-33	5-35
#100 (.15mm)	10	1	0.5	0-6	0-7
#200 (75µm)	10	0	0.0	0-4	0-4
Pan	10	0	0.0		
FM	10	2.13	0.100	2.3	2.1-2.5
-#200 (75um)	1	0.16			
Grad Loss	10	0.010	0.0221		
Wash Loss (#200/75um)	1	0.13			
Total Moisture	9	3.2	0.82		
D10 (ES)	10	0.1988	0.01097		
D50	10	0.46	0.036		
D60	10	0.54	0.047		
Cc	10	1.03	0.036		
Cu	10	2.72	0.170		

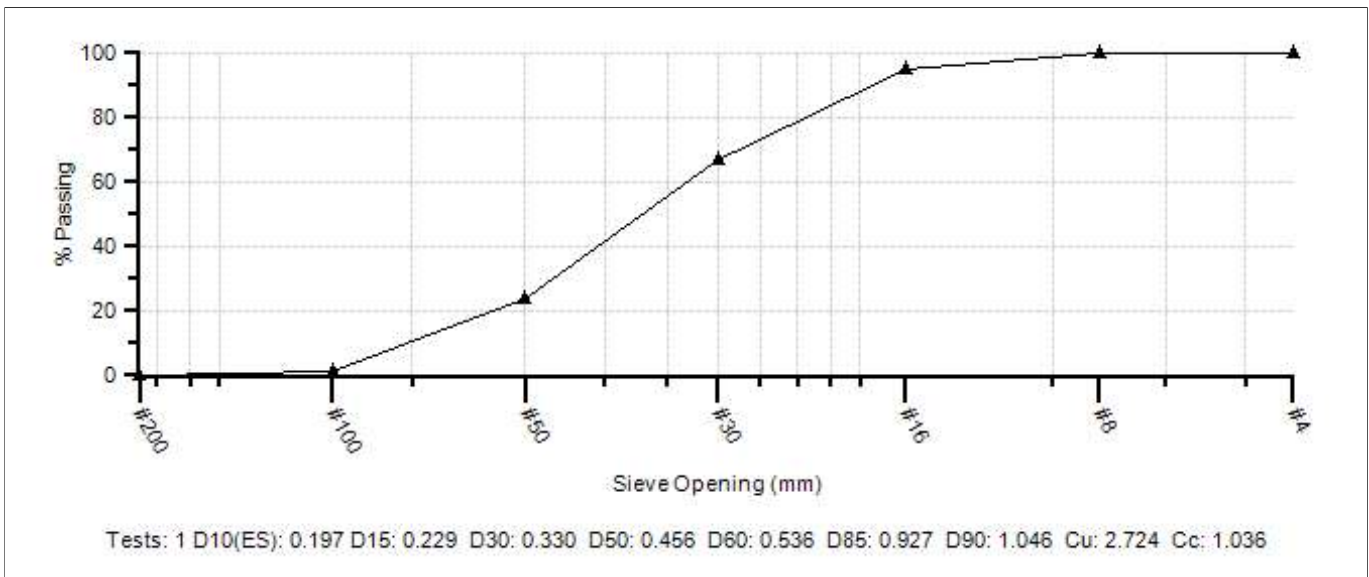

Query

Query Selections

Date Created 05/03/2024

Date Range 04/28/2024 - 05/03/2024

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping