




# Basic Quality Statistical Summary Report

**Plant** 2010-Ortona Sand Company (FDOT Pit # 05-045)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 04/28/2024 - 05/03/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	4	100.0	0.00	95-100	
#8 (2.36mm)	4	100.0	0.06	85-100	
#16 (1.18mm)	4	96.0	0.42	65-99	
#30 (.6mm)	4	54.2	3.66	25-70	
#50 (.3mm)	4	20.1	3.76	5-35	
#100 (.15mm)	4	1.4	0.53	0-7	
#200 (75µm)	4	0.0	0.00		
Pan	4	0.0	0.00		
FM	4	2.28	0.073		
Total Moisture	4	2.9	0.17		
D10 (ES)	4	0.21	0.017		
D50	4	0.56	0.041		
D60	4	0.66	0.038		
D15/D85	4	0.26	0.021		
Cc	4	0.98	0.043		
Cu	4	3.16	0.104		

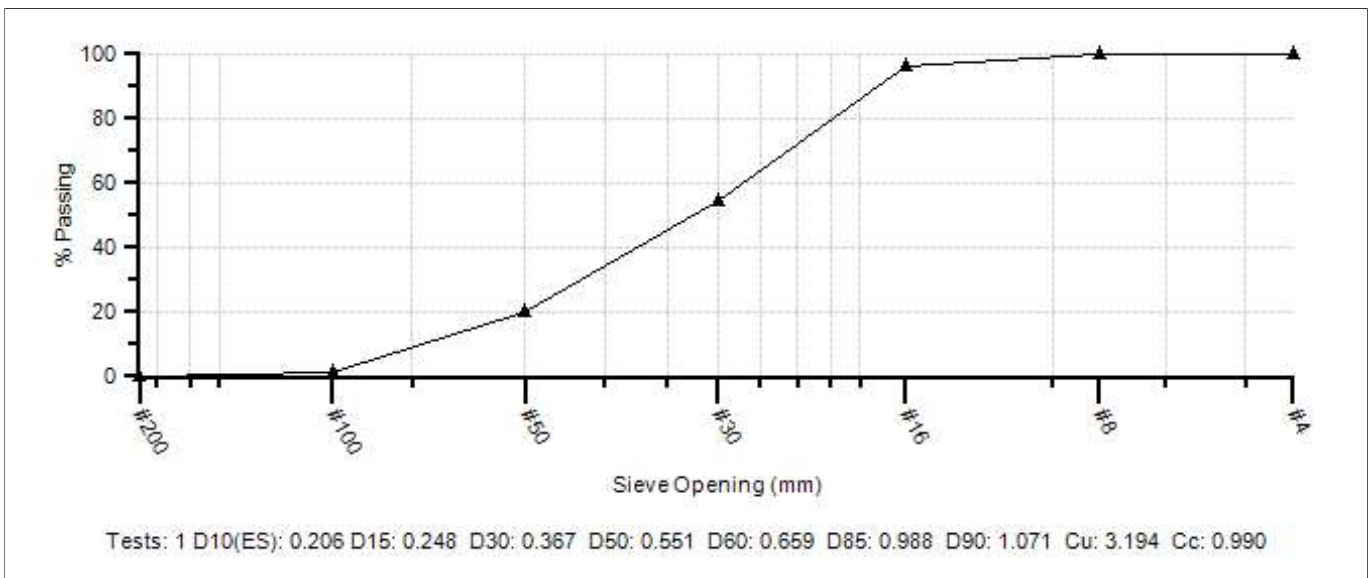

**Query**

Query Selections  
Date Created 05/03/2024  
Date Range 04/28/2024 - 05/03/2024  
Plant Ortona Sand Company (FDOT Pit # 05-045)  
Sample Type Shipping