




Basic Quality Statistical Summary Report

Plant 1030-Haines City Mine (FDOT Pit #16-024)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 04/26/2024 - 05/03/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	6	100.0	0.00	95-100	95-100
#8 (2.36mm)	6	99.9	0.10	85-100	85-100
#16 (1.18mm)	6	96.2	1.26	65-98	65-100
#30 (.6mm)	6	67.7	9.00	25-75	≥25
#50 (.3mm)	6	33.7	6.08	5-44	5-45
#100 (.15mm)	6	6.4	2.43	0-10	0-10
#200 (75µm)	6	0.1	0.06	0-4	0-4
Pan	6	0.0	0.00		
FM	6	1.96	0.150	1.8-2.2\2	
Total Moisture	6	3.2	1.18	0-5	0-6
D10 (ES)	6	0.17	0.012		
D50	6	0.43	0.069		
D60	6	0.52	0.081		
Cc	6	0.90	0.120		
Cu	6	3.16	0.470		

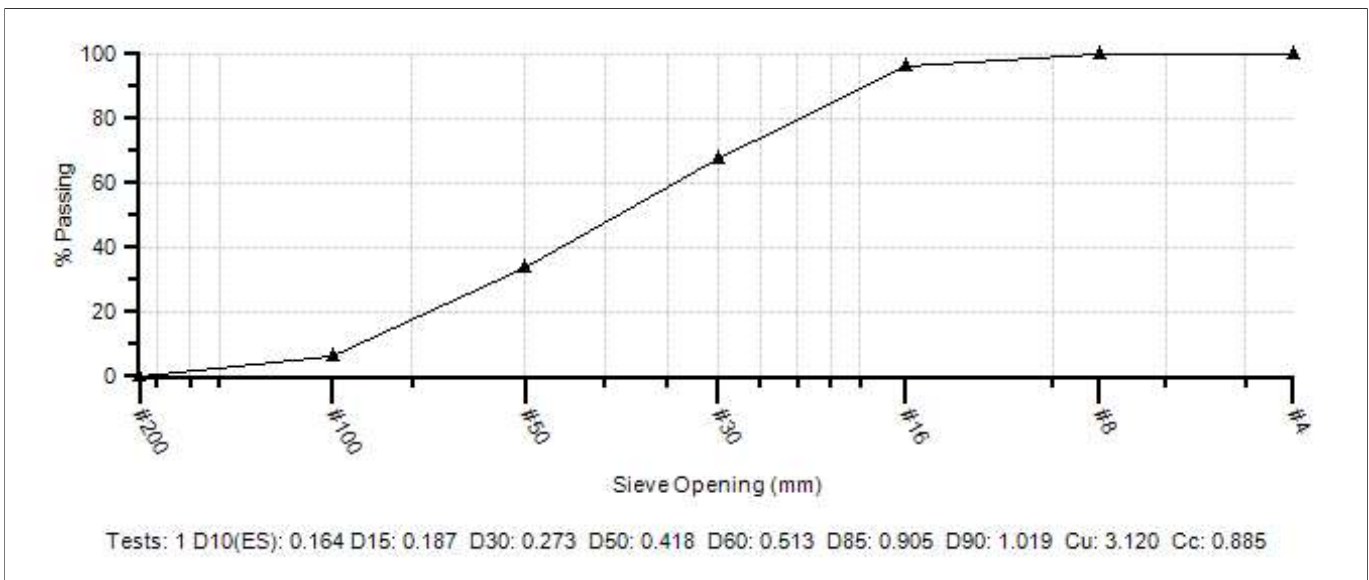

Query

Query Selections
Date Created 05/03/2024
Date Range 04/26/2024 - 05/03/2024
Plant Haines City Mine (FDOT Pit #16-024)
Sample Type Shipping