




# Basic Quality Statistical Summary Report

**Plant** 1030-Haines City Mine (FDOT Pit #16-024)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 08/27/2024 - 09/03/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	6	100.0	0.00	95-100	95-100
#8 (2.36mm)	6	99.9	0.04	85-100	85-100
#16 (1.18mm)	6	96.1	0.73	65-98	65-100
#30 (.6mm)	6	66.6	4.14	25-75	≥25
#50 (.3mm)	6	30.8	6.34	5-44	5-45
#100 (.15mm)	6	6.4	3.14	0-10	0-10
#200 (75µm)	6	0.2	0.08	0-4	0-4
Pan	6	0.0	0.00		
FM	6	2.00	0.118	1.8-2.2\2	
Total Moisture	6	4.7	1.70	0-5	0-6
D10 (ES)	6	0.17	0.019		
D50	6	0.44	0.042		
D60	6	0.53	0.048		
Cc	6	0.95	0.079		
Cu	6	3.17	0.330		

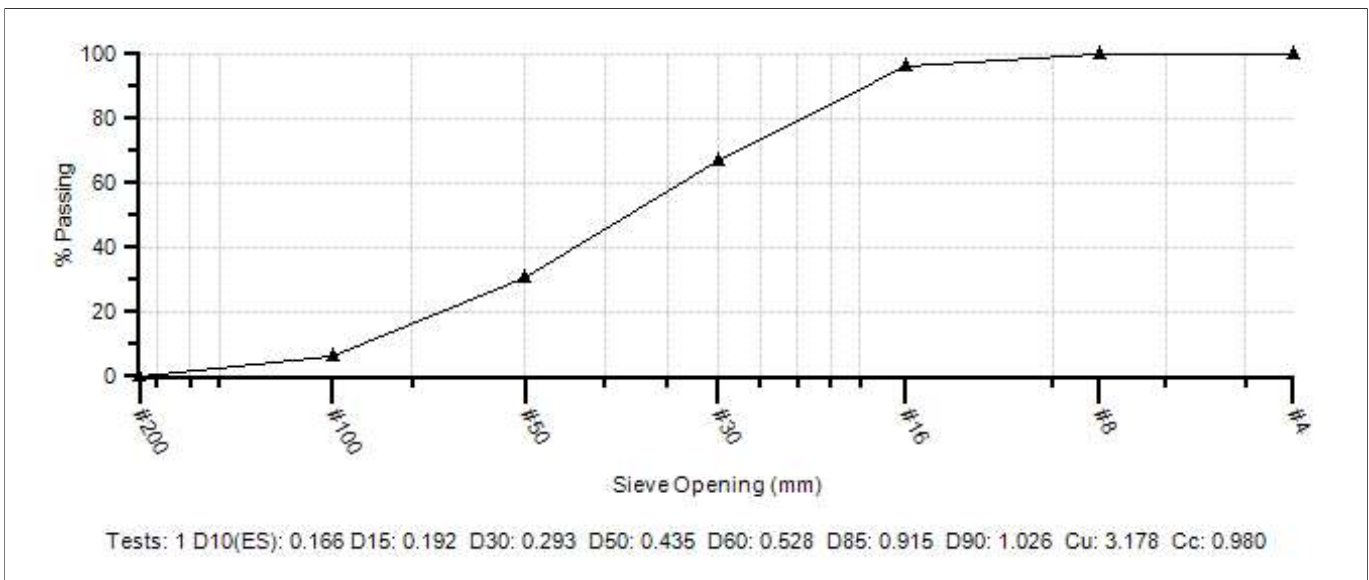

**Query**

Query Selections

Date Created 09/03/2024

Date Range 08/27/2024 - 09/03/2024

Plant Haines City Mine (FDOT Pit #16-024)

Sample Type Shipping