




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1008-Mason Sand
Specification Mason Sand
Period 10/24/2024 - 10/31/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	5	100	0.0	97-100	
#8 (2.36mm)	5	100	0.0	97-100	
#16 (1.18mm)	5	100	0.5	95-100	
#30 (.6mm)	5	97	1.4	85-100	
#50 (.3mm)	5	82	3.6	35-90	
#100 (.15mm)	5	8	1.6	3-35	
#200 (75µm)	5	1.7	0.96		
Pan	5	0.0	0.00		
FM	5	1.13	0.063	0.9-1.4	1.2
Grad Loss	5	0.076	0.0497		
Total Moisture	5	3.5	0.34	0-5.5	0-6
D10 (ES)	5	0.1516	0.00454		
D50	5	0.22	0.005		
D60	5	0.25	0.005		
Cc	5	0.91	0.015		
Cu	5	1.61	0.041		

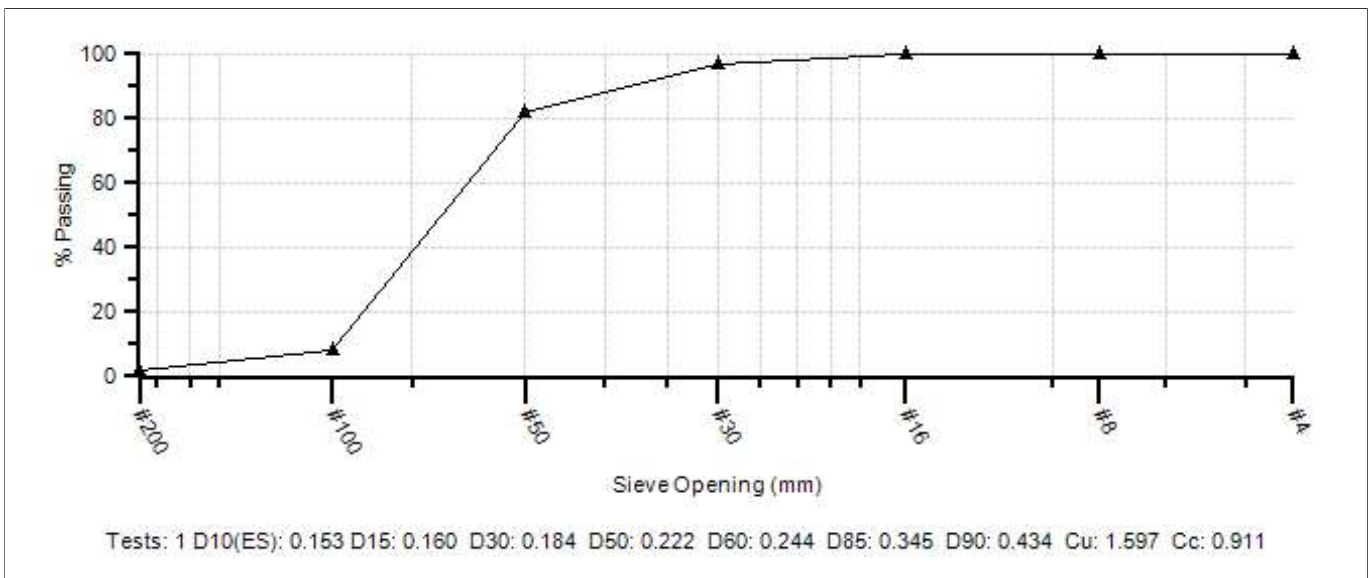

Query

Query Selections

Date Created 10/31/2024

Date Range 10/24/2024 - 10/31/2024

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping