




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 12/23/2024 - 01/03/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	19	100.0	0.00	95-100	
#8 (2.36mm)	19	99.9	0.05	85-100	
#16 (1.18mm)	19	95.2	0.83	65-97	
#30 (.6mm)	19	66.3	2.34	25-75	
#50 (.3mm)	19	30.2	2.81	5-40	
#100 (.15mm)	19	2.4	0.51	0-7	
#200 (75µm)	19	0.0	0.05		
Pan	19	0.0	0.00		
FM	19	2.06	0.045	1.82-2.18\2	1.8-2.2
Grad Loss	19	0.000	0.0000		
Total Moisture	19	3.7	0.63	1-5	1-5
D10 (ES)	19	0.1818	0.00379		
D50	19	0.44	0.019		
D60	19	0.53	0.022		
Cc	19	0.92	0.076		
Cu	19	2.93	0.102		

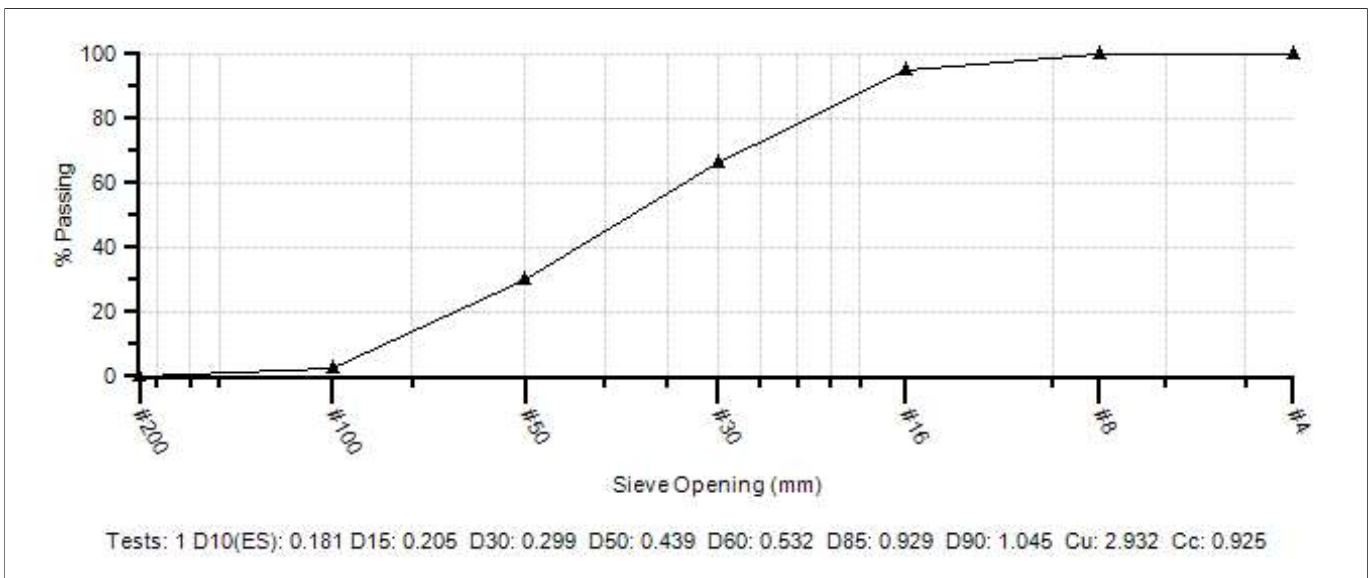

Query

Query Selections

Date Created 01/03/2025

Date Range 12/23/2024 - 01/03/2025

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping