




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 12/23/2024 - 01/03/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	13	100	0.0	95-100	95-100
#8 (2.36mm)	13	100	0.0	85-100	85-100
#16 (1.18mm)	13	95	0.8	67-96	65-97
#30 (.6mm)	13	60	3.1	27-68	25-70
#50 (.3mm)	13	22	2.6	7-33	5-35
#100 (.15mm)	13	1	0.8	0-6	0-7
#200 (75µm)	13	0	0.0	0-4	0-4
Pan	13	0	0.0		
FM	13	2.22	0.045	2.3	2.1-2.5
-#200 (75µm)	2	0.09	0.085		
Grad Loss	13	-0.008	0.0175		
Wash Loss (#200/75µm)	2	0.09	0.085		
Total Moisture	12	3.6	0.93		
Color	2	3	0.0		1-5
D10 (ES)	13	0.2021	0.01030		
D50	13	0.50	0.020		
D60	13	0.60	0.031		
Cc	13	0.99	0.039		
Cu	13	2.97	0.233		

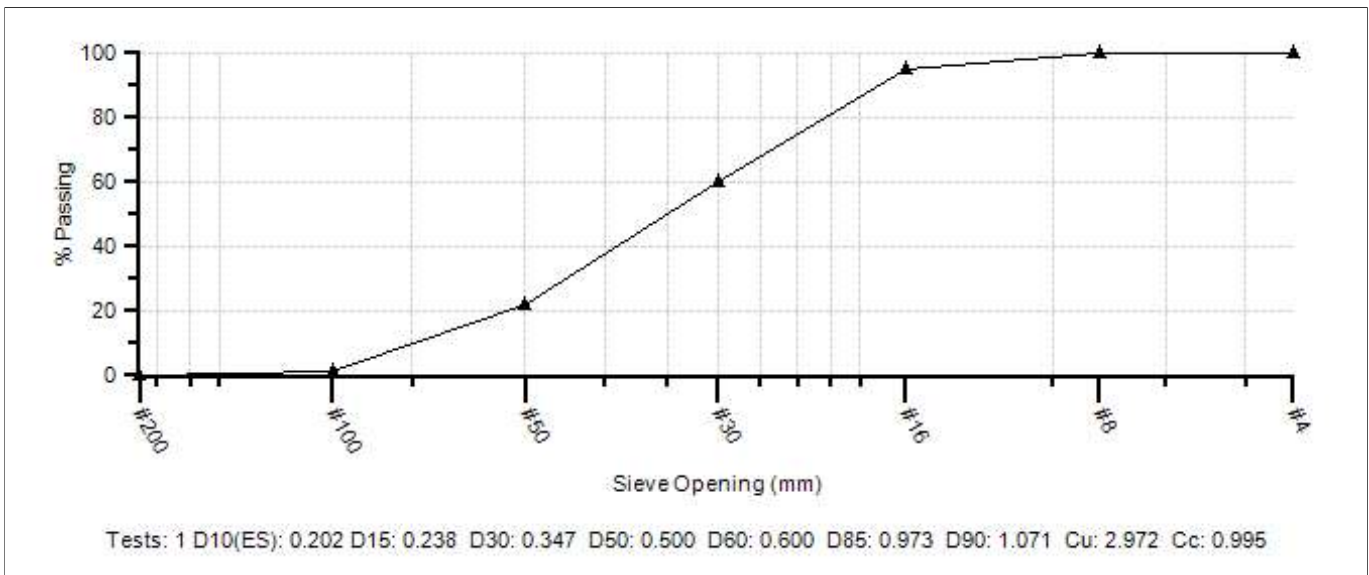

Query

Query Selections

Date Created 01/03/2025

Date Range 12/23/2024 - 01/03/2025

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping