




Basic Quality Statistical Summary Report

Plant 1210-Liberty Sand Mine
Product 117-GDOT 10NS Concrete Sand
Specification GADOT 10NS
Period 12/23/2024 - 01/03/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
3/8" (9.5mm)	6	100.00	0.000		
#4 (4.75mm)	7	99.51	0.237		95-100
#8 (2.36mm)	7	92.39	1.501		
#16 (1.18mm)	7	74.48	3.098		45-95
#30 (.6mm)	7	44.27	3.929		
#50 (.3mm)	7	15.73	7.727		5-30
#100 (.15mm)	7	4.17	2.489		0-10
#200 (75µm)	7	0.15	0.102		0-3
Pan	7	0.00	0.000		
FM	7	2.70	0.141	2.4-2.85\2.65	
Grad Loss	7	0.007	0.0122		
Total Moisture	5	5.2	1.83	0-5\4	0-6
D10 (ES)	7	0.23	0.064		
D50	7	0.68	0.054		
Cu	7	3.90	0.958		

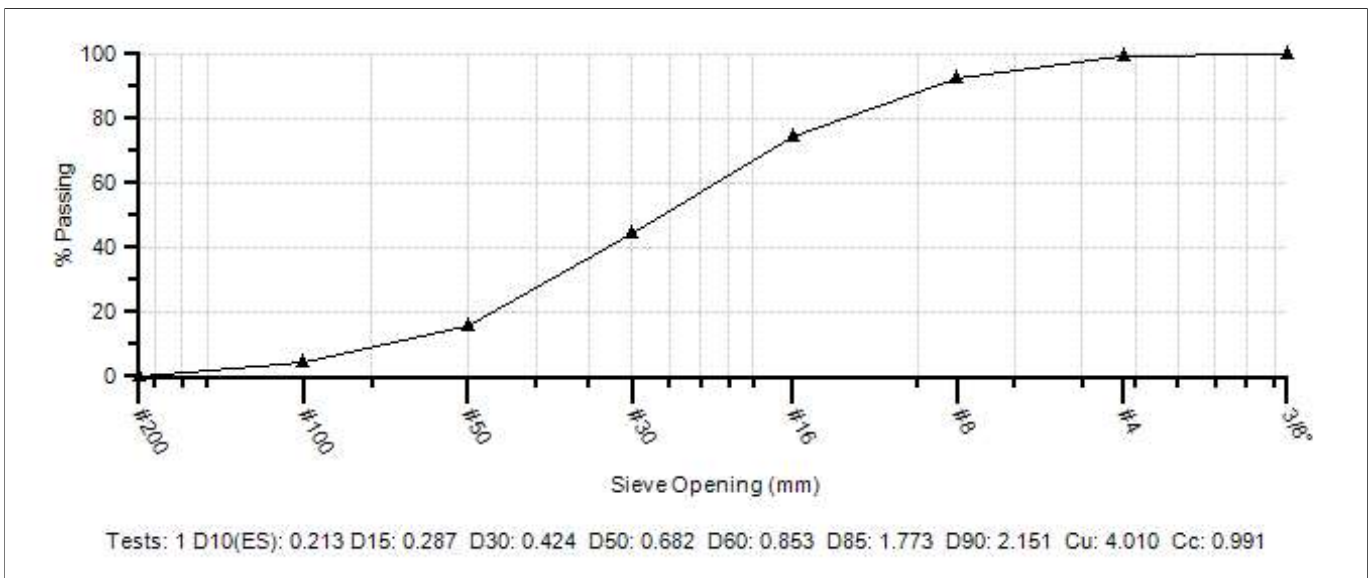

Query

Query Selections
Date Created 01/03/2025
Date Range 12/23/2024 - 01/03/2025
Plant Liberty Sand Mine
Sample Type Shipping