




Basic Quality Statistical Summary Report

Plant 1070-Independent South Mine (FDOT Pit#11-298)
Product 1008-Mason Sand
Specification Mason Sand
Period 04/11/2025 - 04/18/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	4	100	0.0	97-100	
#8 (2.36mm)	4	100	0.0	97-100	
#16 (1.18mm)	4	100	0.0	95-100	
#30 (.6mm)	4	99	0.5	85-100	
#50 (.3mm)	4	96	1.3	35-90	
#100 (.15mm)	4	16	5.0	0-35	
#200 (75µm)	4	0.6	0.29		
Pan	4	0.0	0.00		
FM	4	0.890	0.0684	1.05-1.45\1.2	
Total Moisture	4	6.622	2.3463	0-5	0-6
D10 (ES)	4	0.12	0.016		
D50	4	0.20	0.008		
D60	4	0.22	0.008		
Cc	4	1.10	0.102		
Cu	4	1.86	0.210		

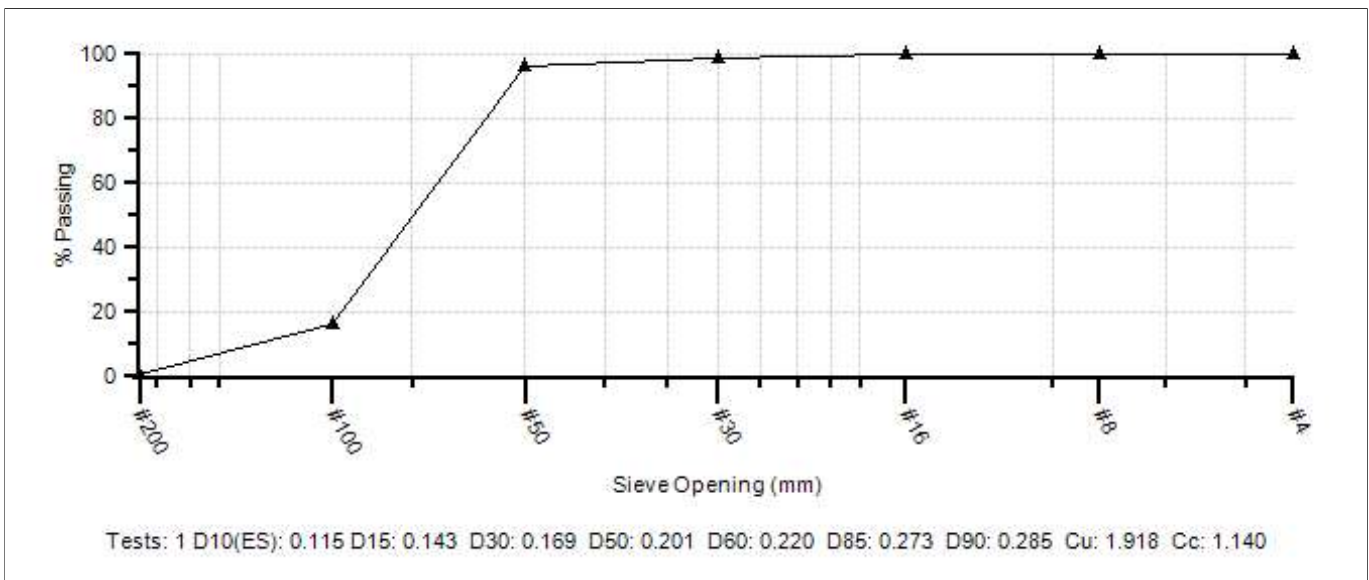

Query

Query Selections
Date Created 04/18/2025
Date Range 04/11/2025 - 04/18/2025
Plant Independent South Mine (FDOT Pit#11-298)
Sample Type Shipping