




# Basic Quality Statistical Summary Report

**Plant** 2010-Ortona Sand Company (FDOT Pit # 05-045)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 03/18/2025 - 04/18/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	20	100.0	0.00	95-100	
#8 (2.36mm)	20	99.9	0.08	85-100	
#16 (1.18mm)	20	95.2	1.08	65-99	
#30 (.6mm)	20	55.5	5.13	25-70	
#50 (.3mm)	20	19.1	4.65	5-35	
#100 (.15mm)	20	1.4	0.79	0-7	
#200 (75µm)	20	0.1	0.16		
Pan	20	0.0	0.00		
FM	20	2.29	0.105		
Total Moisture	20	3.3	0.69		
D10 (ES)	20	0.21	0.035		
D50	20	0.54	0.049		
D60	20	0.64	0.051		
D15/D85	20	0.26	0.033		
Cc	20	1.01	0.118		
Cu	20	3.07	0.405		

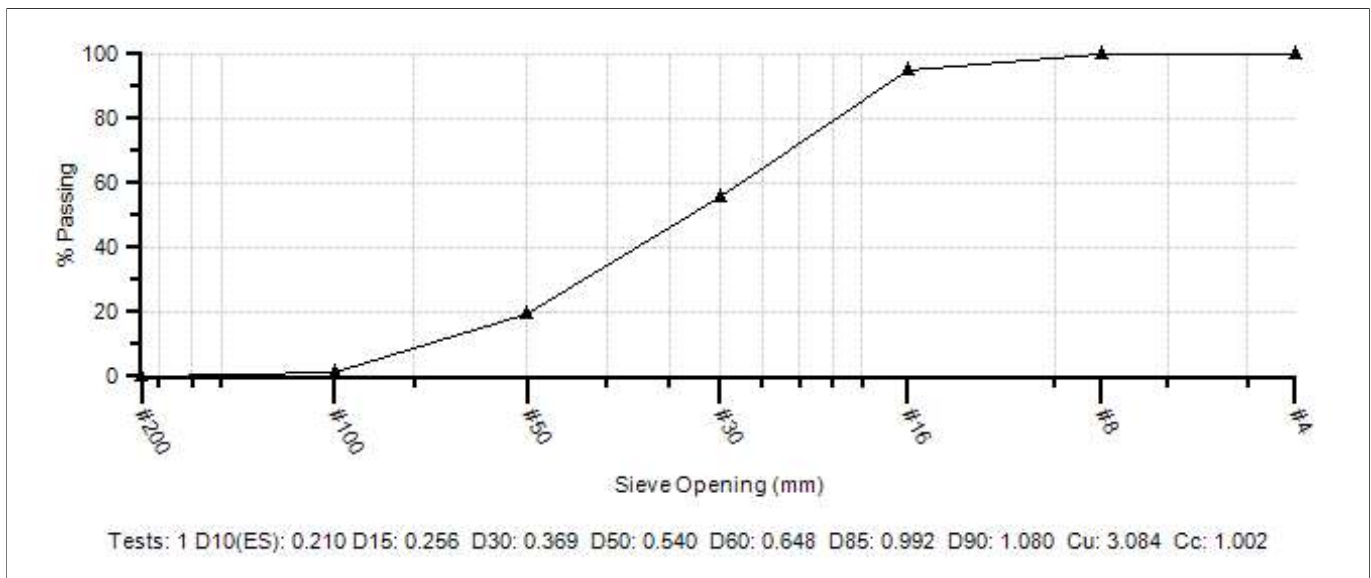

**Query**

Query Selections  
Date Created 04/18/2025  
Date Range 03/18/2025 - 04/18/2025  
Plant Ortona Sand Company (FDOT Pit # 05-045)  
Sample Type Shipping