




# Basic Quality Statistical Summary Report

**Plant** 1030-Haines City Mine (FDOT Pit #16-024)  
**Product** 1001-FDOT Concrete Silica Sand Code F01  
**Specification** FDOT Concrete Silica Sand Code F01  
**Period** 04/18/2025 - 04/25/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	8	100	0.0		95-100
#8 (2.36mm)	8	100	0.0		85-100
#16 (1.18mm)	8	93	0.6		65-97
#30 (.6mm)	8	57	2.5	27-68	25-70
#50 (.3mm)	8	22	1.4	7-34	5-35
#100 (.15mm)	8	4	0.8	0-6	0-7
#200 (75µm)	8	0	0.0		0-4
Pan	8	0	0.0		
FM	8	2.24	0.036	2.05-2.37/2.2	2-2.4
Grad Loss	8	-0.004	0.0099		
Total Moisture	8	1.8	0.74		
D10 (ES)	8	0.19	0.008		
D50	8	0.52	0.026		
D60	8	0.63	0.027		
Cc	8	1.02	0.015		
Cu	8	3.35	0.178		

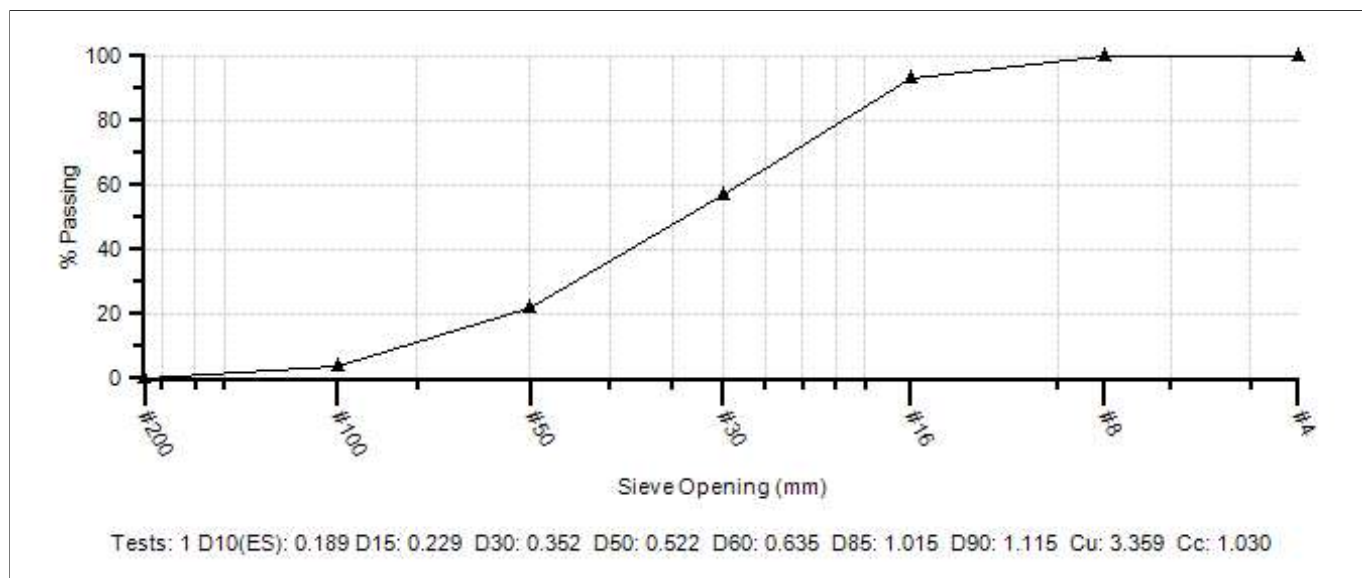

**Query**

Query Selections

Date Created 04/25/2025

Date Range 04/18/2025 - 04/25/2025

Plant Haines City Mine (FDOT Pit #16-024)

Sample Type Shipping