




Basic Quality Statistical Summary Report

Plant 2010-Ortona Sand Company (FDOT Pit # 05-045)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 03/25/2025 - 04/25/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	17	100.0	0.00	95-100	
#8 (2.36mm)	17	99.9	0.08	85-100	
#16 (1.18mm)	17	95.4	1.10	65-99	
#30 (.6mm)	17	56.2	5.29	25-70	
#50 (.3mm)	17	19.5	4.87	5-35	
#100 (.15mm)	17	1.4	0.79	0-7	
#200 (75µm)	17	0.1	0.17		
Pan	17	0.0	0.00		
FM	17	2.28	0.107		
Total Moisture	17	3.4	0.74		
D10 (ES)	17	0.21	0.037		
D50	17	0.54	0.050		
D60	17	0.64	0.053		
D15/D85	17	0.26	0.035		
Cc	17	1.02	0.128		
Cu	17	3.07	0.438		

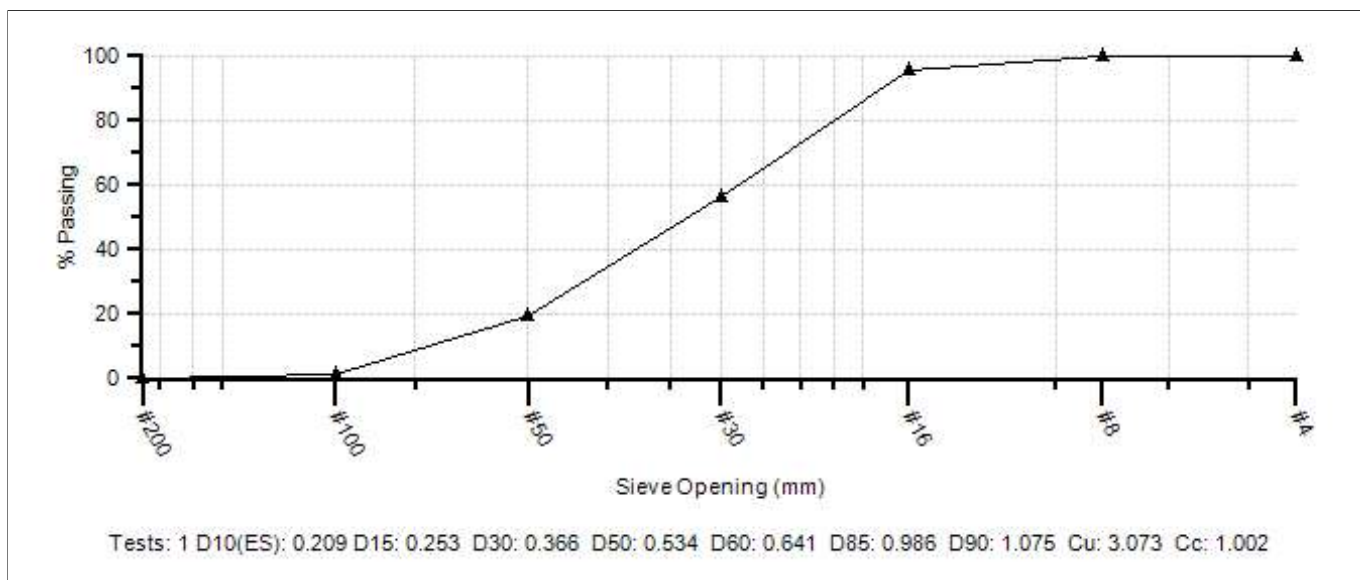

Query

Query Selections

Date Created 04/25/2025

Date Range 03/25/2025 - 04/25/2025

Plant Ortona Sand Company (FDOT Pit # 05-045)

Sample Type Shipping