




Basic Quality Statistical Summary Report

Plant 2010-Ortona Sand Company (FDOT Pit # 05-045)
Product 1008-Mason Sand
Specification Mason Sand
Period 03/25/2025 - 04/25/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	17	100	0.0	100-100	
#8 (2.36mm)	17	100	0.0	100-100	
#16 (1.18mm)	17	100	0.0	97-100	
#30 (.6mm)	17	97	1.7	80-100	
#50 (.3mm)	17	69	6.9	43-85	
#100 (.15mm)	17	6	3.3	0-25	
#200 (75µm)	17	0.2	0.22		
Pan	17	0.0	0.00		
FM	17	1.27	0.092		
Grad Loss	17	0.000	0.0000		
Total Moisture	17	2.4	1.03	0-5	0-6
D10 (ES)	17	0.15	0.011		
D50	17	0.24	0.014		
D60	17	0.27	0.018		
D15/D85	17	0.38	0.042		
Cc	1	0.89			
Cu	17	1.78	0.137		

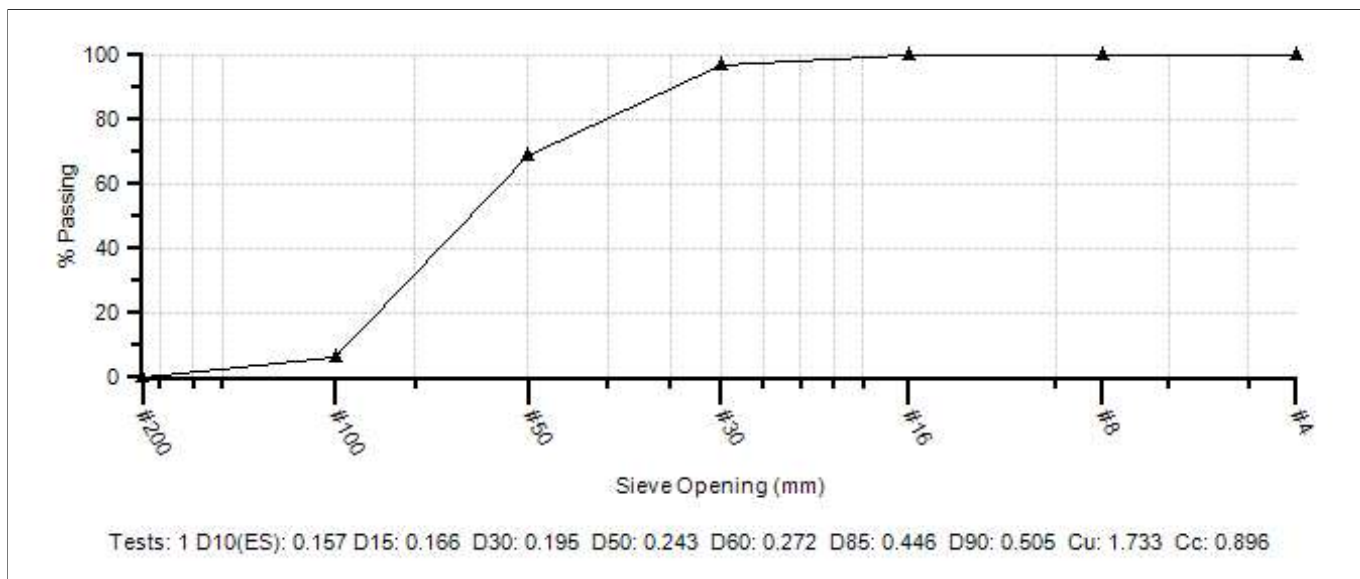

Query

Query Selections

Date Created 04/25/2025

Date Range 03/25/2025 - 04/25/2025

Plant Ortona Sand Company (FDOT Pit # 05-045)

Sample Type Shipping