




Basic Quality Statistical Summary Report

Plant 1030-Haines City Mine (FDOT Pit #16-024)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 05/01/2025 - 05/08/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	6	100.0	0.00	95-100	95-100
#8 (2.36mm)	6	99.9	0.10	85-100	85-100
#16 (1.18mm)	6	96.2	1.29	65-98	65-100
#30 (.6mm)	6	73.5	3.19	25-75	≥25
#50 (.3mm)	6	45.6	3.80	5-44	5-45
#100 (.15mm)	6	9.5	1.89	0-10	0-10
#200 (75µm)	6	0.1	0.04	0-4	0-4
Pan	6	0.0	0.00		
FM	6	1.76	0.076	1.8-2.2\2	
Total Moisture	6	3.9	0.61	0-5	0-6
D10 (ES)	6	0.15	0.013		
D50	6	0.33	0.030		
D60	6	0.43	0.026		
Cc	6	0.78	0.038		
Cu	6	2.90	0.162		

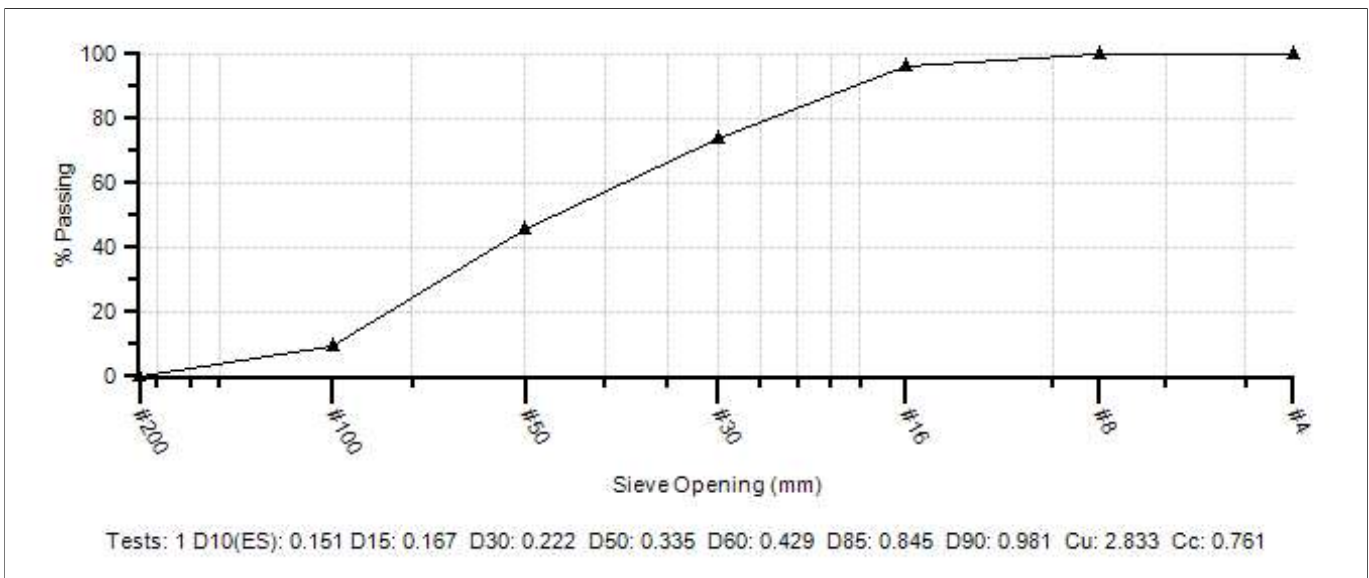

Query

Query Selections

Date Created 05/08/2025

Date Range 05/01/2025 - 05/08/2025

Plant Haines City Mine (FDOT Pit #16-024)

Sample Type Shipping