




# Basic Quality Statistical Summary Report

**Plant** 1030-Haines City Mine (FDOT Pit #16-024)  
**Product** 1001-FDOT Concrete Silica Sand Code F01  
**Specification** FDOT Concrete Silica Sand Code F01  
**Period** 05/23/2025 - 05/30/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	7	100	0.0		95-100
#8 (2.36mm)	7	100	0.0		85-100
#16 (1.18mm)	7	95	0.8		65-97
#30 (.6mm)	7	63	3.3	27-68	25-70
#50 (.3mm)	7	24	4.4	7-34	5-35
#100 (.15mm)	7	4	1.1	0-6	0-7
#200 (75µm)	7	0	0.0		0-4
Pan	7	0	0.0		
FM	7	2.14	0.081	2.05-2.37/2.2	2-2.4
Grad Loss	7	0.010	0.0380		
Total Moisture	6	3.8	1.52		
D10 (ES)	7	0.19	0.019		
D50	7	0.48	0.027		
D60	7	0.57	0.034		
Cc	7	1.04	0.041		
Cu	7	3.04	0.257		

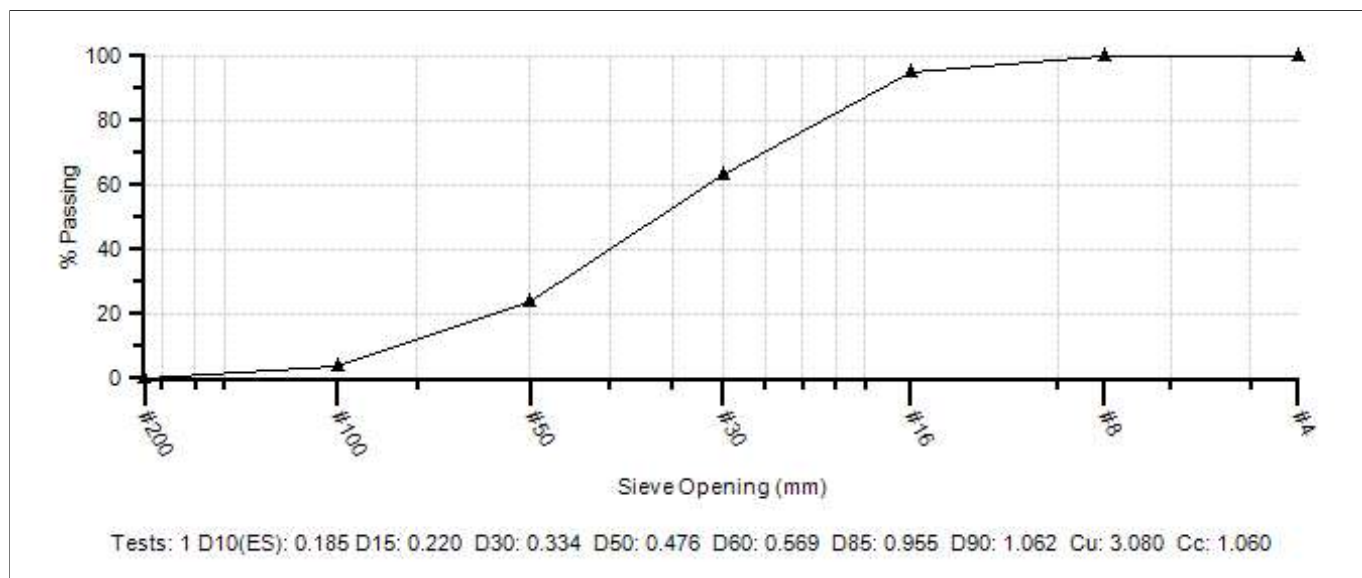

**Query**

Query Selections

Date Created 05/30/2025

Date Range 05/23/2025 - 05/30/2025

Plant Haines City Mine (FDOT Pit #16-024)

Sample Type Shipping