




Basic Quality Statistical Summary Report

Plant 2010-Ortona Sand Company (FDOT Pit # 05-045)
Product 1008-Mason Sand
Specification Mason Sand
Period 05/23/2025 - 05/30/2025

| Sieve/Test | Tests | Average | St Dev | Target | Specification |
|----------------|-------|---------|--------|---------|---------------|
| #4 (4.75mm) | 3 | 100 | 0.0 | 100-100 | |
| #8 (2.36mm) | 3 | 100 | 0.0 | 100-100 | |
| #16 (1.18mm) | 3 | 100 | 0.0 | 97-100 | |
| #30 (.6mm) | 3 | 97 | 2.1 | 80-100 | |
| #50 (.3mm) | 3 | 76 | 4.7 | 43-85 | |
| #100 (.15mm) | 3 | 8 | 1.2 | 0-25 | |
| #200 (75µm) | 3 | 0.0 | 0.06 | | |
| Pan | 3 | 0.0 | 0.00 | | |
| FM | 3 | 1.18 | 0.078 | | |
| Grad Loss | 3 | 0.010 | 0.0167 | | |
| Total Moisture | 3 | 6.8 | 3.12 | 0-5 | 0-6 |
| D10 (ES) | 3 | 0.15 | 0.000 | | |
| D50 | 3 | 0.23 | 0.010 | | |
| D60 | 3 | 0.25 | 0.006 | | |
| D15/D85 | 3 | 0.41 | 0.042 | | |
| Cu | 3 | 1.67 | 0.047 | | |

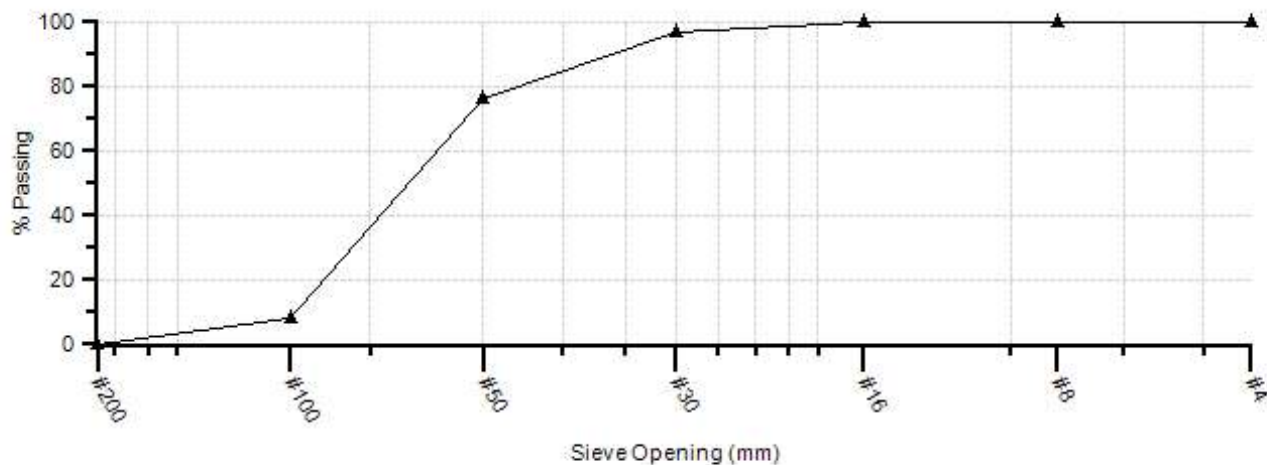

Query

Query Selections

Date Created 05/30/2025

Date Range 05/23/2025 - 05/30/2025

Plant Ortona Sand Company (FDOT Pit # 05-045)

Sample Type Shipping