




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 06/02/2025 - 06/09/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	13	100	0.0	95-100	95-100
#8 (2.36mm)	13	100	0.0	85-100	85-100
#16 (1.18mm)	13	96	1.0	67-96	65-97
#30 (.6mm)	13	64	6.2	27-68	25-70
#50 (.3mm)	13	21	4.5	7-33	5-35
#100 (.15mm)	13	1	0.6	0-6	0-7
#200 (75µm)	13	0	0.0	0-4	0-4
Pan	13	0	0.0		
FM	13	2.18	0.107	2.3	2.1-2.5
Grad Loss	13	0.017	0.0379		
Total Moisture	12	3.8	1.02		
D10 (ES)	13	0.2103	0.02192		
D50	13	0.48	0.049		
D60	13	0.56	0.058		
Cc	13	1.02	0.041		
Cu	13	2.69	0.249		

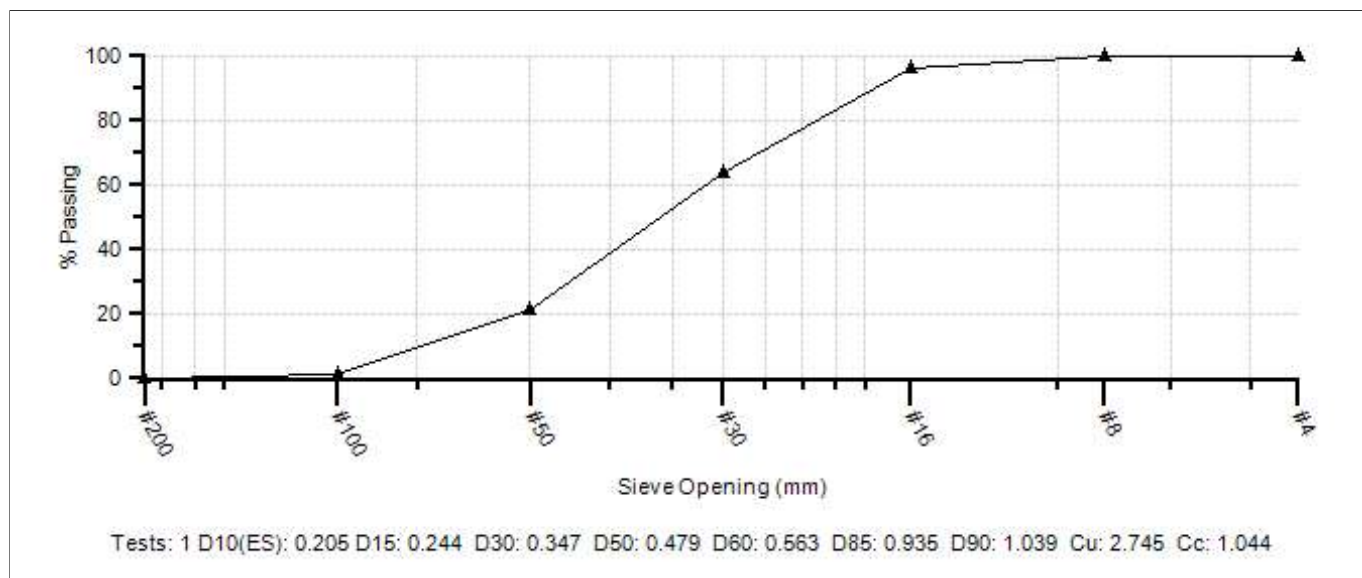

Query

Query Selections

Date Created 06/09/2025

Date Range 06/02/2025 - 06/09/2025

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping