




# Basic Quality Statistical Summary Report

**Plant** 2010-Ortona Sand Company (FDOT Pit # 05-045)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 06/02/2025 - 06/09/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	7	100.0	0.00	95-100	
#8 (2.36mm)	7	99.9	0.13	85-100	
#16 (1.18mm)	7	96.1	2.60	65-99	
#30 (.6mm)	7	63.4	18.14	25-70	
#50 (.3mm)	7	32.9	23.22	5-35	
#100 (.15mm)	7	2.8	2.89	0-7	
#200 (75µm)	7	0.1	0.08		
Pan	7	0.0	0.00		
FM	7	2.05	0.465		
Total Moisture	7	4.2	0.59		
D10 (ES)	7	0.20	0.037		
D50	7	0.47	0.143		
D60	7	0.56	0.168		
D15/D85	7	0.28	0.093		
Cc	7	0.93	0.086		
Cu	7	2.84	0.566		

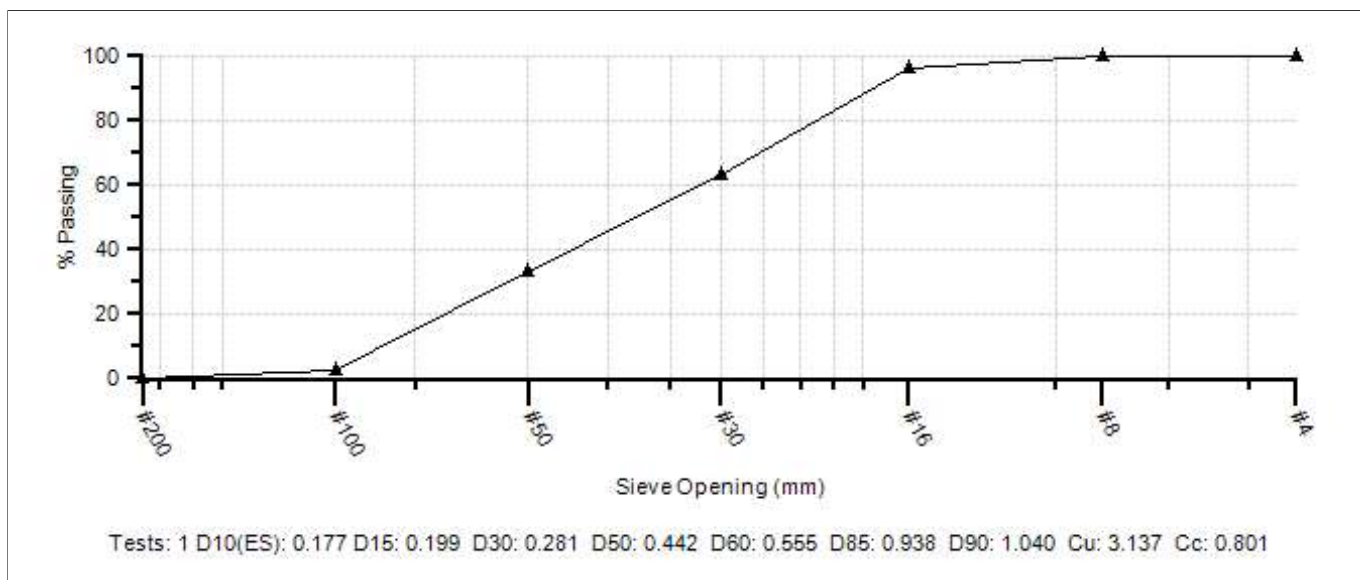

**Query**

Query Selections

Date Created 06/09/2025

Date Range 06/02/2025 - 06/09/2025

Plant Ortona Sand Company (FDOT Pit # 05-045)

Sample Type Shipping