




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 09/11/2026 - 09/18/2026

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	22	100.0	0.00	95-100	
#8 (2.36mm)	22	100.0	0.03	85-100	
#16 (1.18mm)	22	96.9	0.56	65-97	
#30 (.6mm)	22	77.4	2.66	25-75	
#50 (.3mm)	22	35.3	7.25	5-40	
#100 (.15mm)	22	5.5	2.75	0-7	
#200 (75µm)	22	0.0	0.05		
Pan	22	0.0	0.00		
FM	22	1.848	0.0732	1.82-2.18\2	1.8-2.2
Total Moisture	22	3.550	1.1798	1-5	1-5

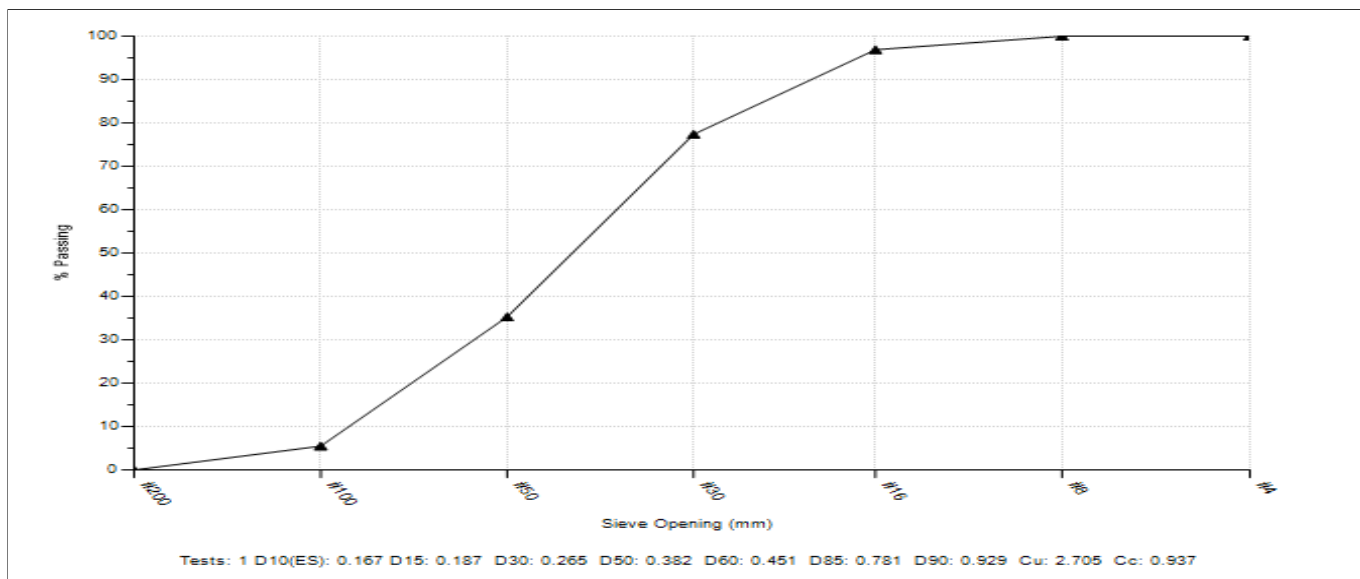

Query

Query Selections

Date Created 09/18/2026

Date Range 09/11/2026 - 09/18/2026

Plant Green Bay Mine (FDOT Pit #16-608)

Product

Specification Auto-Default

Number of Tests 30